

External wall - awmhi01a-03

external wall, solid wood construction, ventilated, with dry lining, with cladding, Gipsplatte

Performance rating

Fire protection performance	REI from inside	90
	REI from outside	60

Maximum ceiling height = 3 m; maximum load $E_{d,fi} = 35,0 \text{ kN/lfm}$
 Classified by HFA

Germany

REI 60 (from inside/from outside); Attention: REI 90 (from inside) possible with 2x12,5mm gypsum plaster board type DF/gypsum fibre board
 Load $E_{d,fi}$ according to the German certification document
 Corresponding proof: manufacturer specific

Thermal performance	U	0.12 W/(m ² K)
	Diffusion	suitable


Calculated by TUM

Acoustic performance	$R_w (C;C_{tr})$	56(-2;-7) dB
	$L_{n,w} (C_i)$	

Assessed by HFA
 Assessed by Müller-BBM

Mass per unit area	m	95.50 kg/m ²
---------------------------	----------	-------------------------

Calculation based on gypsum plaster board type DF

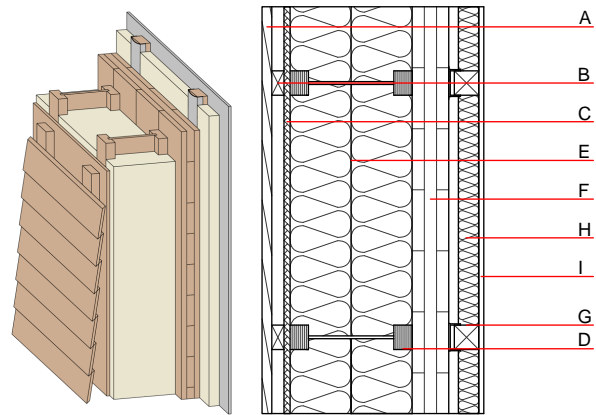

Note: Attention: REI 90 (from inside) in Germany possible with 2x12,5mm gypsum plaster board type DF/gypsum fibre board

Register of building materials used for this application, cross-section (from outside to inside, dimensions in mm)

	Thickness	Building material	Thermal performance				Reaction to fire EN
			λ	μ min – max	ρ	c	
A	24.0	larch wood external wall cladding	0.120	50	450	1.600	D
B	30.0	spruce wood battens offset (30/60) - ventilation	0.120	50	450	1.600	D
C	15.0	fibreboard (MDF)	0.140	11	600	1.700	D
D	300.0	Light composite wood-based beams (I-beams) with solid wood flanges (60/45) and hard board intermediate web ($\geq 6,7$) e=625	0.400	20 - 30	800	1.700	D
E	300.0	mineral wool [040; 11; <1000°C]	0.040	1	11	1.030	A1
F	100.0	cross laminated timber (at least 3-layers, top layer at least 30mm)	0.130	50	500	1.600	D
G	70.0	spruce wood battens 60/60 on resilient clips, e=625	0.120	50	450	1.600	D
H	50.0	mineral wool [040; 11; <1000°C]	0.040	1	11	1.030	A1
I	12.5	gypsum plaster board type DF or	0.250	10	800	1.050	A2
I	12.5	gypsum fibre board	0.320	21	1000	1.100	A2

Sustainability rating (per m²)

Database ecoinvent

O13_{kon}	39.0
--------------------------	------

Calculated by HFA

Database GaBi (ÖKOBAUDAT)

Built-in renewable materials	kg	82.210
Biogenic carbon in kg CO₂-e.	kg CO ₂	117.790
Energy use of Primary Energy	MJ	1196.880
Share of renewable PE	%	39.92

Calculated by TUM

Details of sustainability rating

Database ecoinvent

Lifecycle (Phases)	GWP [kg CO ₂ -e.]	AP [kg SO ₂ -e.]	EP [kg PO ₄ -e.]	ODP [kg R11-e.]	POCP [kg Ethen-e.]	
A1 - A3		0.213	0.093	3,65E-6	0.055	

Lifecycle (Phases)	PERE [MJ]	PERM [MJ]	PERT [MJ]	PENRE [MJ]	PENRM [MJ]	PENRT [MJ]
A1 - A3	111.274	1224.177	1335.451	703.347	36.238	739.585

Database GaBi (ÖKOBAUDAT)

Lifecycle (Phases)	GWP [kg CO ₂ -e.]	AP [kg SO ₂ -e.]	EP [kg PO ₄ -e.]	ODP [kg R11-e.]	POCP [kg Ethen-e.]	
A1 - A3		0.200	0.036	4,51E-6	0.032	
C1 - C4		0.004	0.004	1,96E-7	0.001	
A1 - C4		0.206	0.040	4,71E-6	0.032	

Lifecycle (Phases)	PERE [MJ]	PERM [MJ]	PERT [MJ]	PENRE [MJ]	PENRM [MJ]	PENRT [MJ]
A1 - A3	476.396	1383.888	1856.955	691.437	47.947	738.880
C1 - C4	0.990	-1377.285	-1376.295	20.467	-22.975	-2.510
A1 - C4	477.779	6.862	481.312	719.097	25.024	743.610