

Designation: awmoho02a-01 8/2/23 Last updated:

Holzforschung Austria Source:

Editor: HFA, SP


External wall - awmoho02a-01

external wall, solid wood construction, not ventilated, without dry lining, with cladding, wooden surface

Performance rating

Fire protection **REI** from inside **REI** from outside 30 performance maximum ceiling height = 3 m; maximum load $E_{d,fi}$ = 35,0 kN/m Classified by HFA

Thermal performance	U Diffusion	0.39 W/(m ² K) suitable
Calculated by HFA		
Acoustic performance	R _w (C;C _{tr}) L _{n,w} (C _l)	49(-2;-6) dB
Assessed by TU-GRAZ		
Mass per unit area	m	75.40 kg/m ²

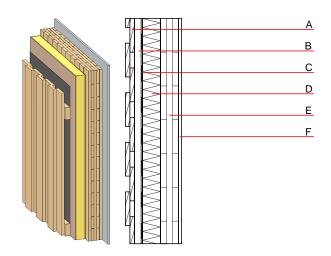

Note: When using cross laminated timber: Variation 00-03: d ≥ 78,0; at least 3-layers, top layer at least 25mm; variation 04: d \geq 94,0; at least 3-layers, top layer at least 30mm

Register of building materials used for this application, cross-section (from outside to inside, dimensions in mm)

	Thickness	Building material	Thermal performance Reaction to f				Reaction to fire
			λ	μ min – max	ρ	С	EN
Α	20.0	larch wood external wall cladding	0.155	150	600	1.600	D
В	30.0	spruce wood battens	0.120	50	450	1.600	D
С		vapour-permeable membrane $sd \le 0.3 m$					
D	75.0	multilayer wood wool composite board (WW-MW-WW)	0.049	2 - 5	130	1.000	В
E	80.0	solid glued wood (e.g. cross laminated timber)	0.130	50	500	1.600	D
F	12.5	gypsum fibre board or 12,5 mm DF	0.320	21	1000	1.100	A2

Sustainability rating (per m²)

Database ecoinvent

OI3_{Kon} 42.1

Calculated by HFA



Designation: awmoho02a-01 Last updated:

8/2/23 Holzforschung Austria Source:

Editor: HFA, SP

Details of sustainability rating

Database ecoinvent

Lifecycle	GWP	AP	EP	ODP	POCP	
(Phases)	[kg CO ₂ -e.]	[kg SO ₂ -e.]	[kg PO ₄ -e.]	[kg R11-e.]	[kg Ethen-e.]	
A1 - A3		0.217	0.077	2,64E-6	0.081	
Lifecycle	PERE	PERM	PERT	PENRE	PENRM	PENRT
(Phases)	[MJ]	[MJ]	[MJ]	[MJ]	[MJ]	[MJ]
A1 - A3	66,254	761.837	828.091	572.699	19.804	592.503