

Designation: awmoho02a-03 Last updated: 8/2/23

Source: Holzforschung Austria


Editor: HFA, SP

## External wall - awmoho02a-03

external wall, solid wood construction, not ventilated, without dry lining, with cladding, wooden surface

#### Performance rating

Thermal performance  Calculated by HFA	U Diffusion	0.35 W/(m <sup>2</sup> K) suitable
Acoustic performance  Assessed by TU-GRAZ	R <sub>w</sub> (C;C <sub>tr</sub> ) L <sub>n,w</sub> (C <sub>l</sub> )	42(-3;-8) dB
Mass per unit area	m	82.90 kg/m <sup>2</sup>

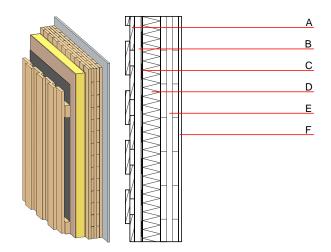

Note: When using cross laminated timber: Variation 00-03: d  $\geq$  78,0; at least 3-layers, top layer at least 25mm; variation 04: d  $\geq$  94,0; at least 3-layers, top layer at least 30mm F=12,5

# Register of building materials used for this application, cross-section (from outside to inside, dimensions in mm)

	Thickness	Building material	Thermal pe	rformance			Reaction to fire	
			λ	μ min – max	ρ	С	EN	
Α	20.0	larch wood external wall cladding	0.155	150	600	1.600	D	
В	30.0	spruce wood battens	0.120	50	450	1.600	D	
С		vapour-permeable membrane $sd \le 0,3m$						
D	100.0	wood-fibre insulation board [055; 200]	0.055	5 - 7	200	2.100	Е	
Е	80.0	solid glued wood (e.g. cross laminated timber)	0.130	50	500	1.600	D	
F	12.5	gypsum fibre board or 12,5 mm DF	0.320	21	1000	1.100	A2	

### Sustainability rating (per m<sup>2</sup>)

Database ecoinvent

Ol3<sub>Kon</sub> 38.4

Calculated by HFA



Designation: awmoho02a-03 8/2/23 Holzforschung Austria Last updated:

Source:

Editor: HFA, SP

## Details of sustainability rating

#### Database ecoinvent

Lifecycle	GWP	AP	EP	ODP	POCP	
(Phases)	[kg CO <sub>2</sub> -e.]	[kg SO <sub>2</sub> -e.]	[kg PO <sub>4</sub> -e.]	[kg R11-e.]	[kg Ethen-e.]	
A1 - A3		0.192	0.086	3,62E-6	0.047	
Lifecycle	PERE	PERM	PERT	PENRE	PENRM	PENRT
(Phases)	[MJ]	[MJ]	[MJ]	[MJ]	[MJ]	[MJ]
A1 - A3	104.868	1144.204	1249.072	689.940	58.534	748.473