

Designation: awmoho03a-02 Last updated: 8/2/23

Source: Holzforschung Austria

Editor: HFA, PLB

# External wall - awmoho03a-02

external wall, solid wood construction, ventilated, without dry lining, with cladding, wooden surface

### Performance rating

Fire protection REI from inside 60 performance REI from outside 60

maximum ceiling height = 3 m; maximum load  $\rm E_{d,fi}$  = 35,0 kN/m Classified by MA39/HFA


#### Germany

REI 60 (from inside/from outside)

Load E<sub>d.fi</sub> according to the German certification document

Corresponding proof: manufacturer-specific

Thermal performance	U Diffusion	0.19 W/(m <sup>2</sup> K) suitable
Calculated by TUM		
Acoustic performance	R <sub>w</sub> (C;C <sub>tr</sub> ) L <sub>n,w</sub> (C <sub>l</sub> )	43(-1;-4) dB
Assessed by TU-GRAZ Assessed by Müller-BBM		
Mass per unit area	m	95.20 kg/m <sup>2</sup>

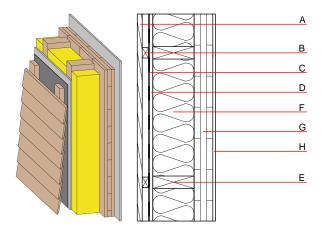

Note: Cross laminated timber: Variation 00-02 and 04-06: at least 3-layers, top layer at least 30mm; variation 03:  $d \ge 85$ ,0; at least 5-layers, top layer at least 17 mm

### Register of building materials used for this application, cross-section (from outside to inside, dimensions in mm)

	Thickness	Building material	Thermal per	Thermal performance			
			λ	μ min – max	ρ	С	EN
Α	24.0	larch wood external wall cladding	0.155	150	600	1.600	D
В	30.0	spruce wood battens (30/60)	0.120	50	450	1.600	D
С		vapour-permeable membrane sd ≤ 0,3 m					
D	15.0	gypsum fibre board	0.320	21	1000	1.100	A2
E	200.0	construction timber (60/200; e= 625)	0.120	50	450	1.600	D
F	200.0	cellulose fibre [R=50; r>5]	0.040	1	50	2.000	В
G	100.0	cross laminated timber	0.130	50	500	1.600	D
Н		without gypsum board lining					

# Sustainability rating (per m²)

Database ecoinvent	Database Ga	
OI3 <sub>Kon</sub>	29.9	Built-in renev
Calculated by HFA		Biogenic carl

Database GaBi (Öl	KOBAUDAT)
-------------------	-----------

Built-in renewable materials	kg	80.010
Biogenic carbon in kg CO <sub>2</sub> -e.	kg CO <sub>2</sub>	113.460
Energy use of Primary Energy	MJ	706.510
Share of renewable PE	%	41.12

Calculated by TUM



Designation: awmoho03a-02 Last updated:

8/2/23 Holzforschung Austria Source:

Editor: HFA, PLB

## Details of sustainability rating

#### Database ecoinvent

Lifecycle	GWP	AP	EP	ODP	POCP	
(Phases)	[kg CO <sub>2</sub> -e.]	[kg SO <sub>2</sub> -e.]	[kg PO <sub>4</sub> -e.]	[kg R11-e.]	[kg Ethen-e.]	
A1 - A3		0.182	0.078	3,15E-6	0.052	
Lifecycle	PERE	PERM	PERT	PENRE	PENRM	PENRT
(Phases)	[MJ]	[MJ]	[MJ]	[MJ]	[MJ]	[MJ]
A1 - A3	125.249	1179,478	1304.727	573.754	23.584	597.338

### Database GaBi (ÖKOBAUDAT)

Lifecycle	GWP	AP	EP	ODP	POCP
(Phases)	[kg CO <sub>2</sub> -e.]	[kg SO <sub>2</sub> -e.]	[kg PO <sub>4</sub> -e.]	[kg R11-e.]	[kg Ethen-e.]
A1 - A3		0.092	0.018	2,88E-6	0.018
C1 - C4		0.006	0.007	2,14E-7	0.001
41 - C4		0.100	0.025	3,10E-6	0.019

Lifecycle	PERE	PERM	PERT	PENRE	PENRM	PENRT
(Phases)	[MJ]	[MJ]	[MJ]	[MJ]	[MJ]	[MJ]
A1 - A3	289.300	1318.130	1605.570	388.580	34.910	423.060
C1 - C4	0.770	-1163.670	-1162.900	20.780	-0.100	20.680
A1 - C4	290.550	154.720	443.410	415.960	34.880	450.400