# dataholz.eu

Designation: Last updated: Source: Editor: awmoho05a-00 8/2/23 Holzforschung Austria HFA, PLB

# External wall - awmoho05a-00

external wall, solid wood construction, ventilated, without dry lining, with cladding, wooden surface


### Performance rating

Fire protection performance	REI from inside REI from outside	60 90
maximum ceiling height = Classified by HFA	3 m; maximum load E <sub>d,f</sub>	<sub>i</sub> = 35,0 kN∕m
Thermal performance	U Diffusion	0.17 W∕(m <sup>2</sup> K) suitable
Calculated by HFA		
Acoustic performance	R <sub>w</sub> (C;C <sub>tr</sub> ) L <sub>n,w</sub> (C <sub>l</sub> )	43 dB
With 12,5 mm gypsum pla Assessed by TU-GRAZ	aster board type DF / gyj	osum fibre board : $R_w \ge 45$

m

Mass per unit area

107.40 kg/m<sup>2</sup>

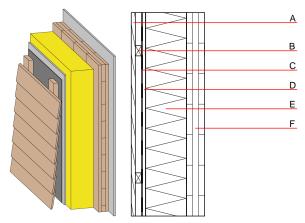

Note: Cross laminated timber:

Variation 00-01: d  $\geq$  94,0; at least 3-layers, top layer at least 30mm; variation 02: d  $\geq$  85,0; at least 5-layers, top layer at least 17 mm G: without plaster board

Register of building materials used for this application, cross-section (from outside to inside, dimensions in mm)

	Thickness	Building material	Thermal pe	rformance			Reaction to fire
			λ	µ min – max	ρ	с	EN
A	20.0	larch wood external wall cladding	0.155	150	600	1.600	D
В	30.0	spruce wood battens	0.120	50	450	1.600	D
С		vapour-permeable membrane $sd \le 0.3m$					
D	12.5	gypsum fibre board	0.320	21	1000	1.100	A2
E	200.0	wood-fibre insulation board [0,040; R=160]	0.042	5 - 7	160	2.100	E
F	100.0	cross laminated timber	0.130	50	500	1.600	D
G		without gypsum board lining					

## Sustainability rating (per m<sup>2</sup>)

#### Database ecoinvent

OI3<sub>Kon</sub>

40.7

calculated with gypsum plaster fire protection board (GKF/DF); this data includes 3-, 5-, and 7-ply cross laminated timber elements; Calculated by HFA

# dataholz.eu

Designation: Last updated: Source: Editor: awmoho05a-00 8/2/23 Holzforschung Austria HFA, PLB

## Details of sustainability rating

#### Database ecoinvent

Lifecycle	GWP	AP	EP	ODP	POCP	
(Phases)	[kg CO <sub>2</sub> -e.]	[kg SO <sub>2</sub> -e.]	[kg PO <sub>4</sub> -e.]	[kg R11-e.]	[kg Ethen-e.]	
A1 - A3		0.204	0.090	3,90E-6	0.052	
1 if a sural a	PERE	PERM	PERT	PENRE	PENRM	PENRT
Lifecycle						
(Phases)	[LM]	[MJ]	[LM]	[LM]	[MJ]	[MJ]

dataholz.eu – Catalogue of timber building materials, components and component connections reviewed to consider thermal, acoustic, fire performance requirements and ecological drivers for timber construction released by accredited testing institutes. These datasheets will generally be accepted as proofs of compliance by building authorities.