

Designation: awrhhi03a-11 Last updated: 8/2/23

Holzforschung Austria Source:

Editor: HFA, SP

## External wall - awrhhi03a-11

external wall, timber frame construction, ventilated, with dry lining, with cladding, other surface

## Performance rating

**REI** from inside 60 Fire protection performance REI from outside 30 maximum ceiling height = 3 m; maximum load  $E_{d,fi}$  = 19,2 kN/m Classified by HFA


Thermal performance	U Diffusion	0.23 W/(m <sup>2</sup> K) suitable
Calculated by HFA		
Acoustic performance	R <sub>w</sub> (C;C <sub>tr</sub> ) L <sub>n,w</sub> (C <sub>l</sub> )	50(-3;-10) dB

Battens for the ventilation space screwed onto the structural timber together with vertical battens for the dry lining screwed directly onto the ledger beams will result in Rw(C;Ctr)=43(-1;-5) dB Assessed by MA39

Mass per unit area  $51.30 \text{ kg/m}^2$ 

Calculation based on GF

Calculated by HFA

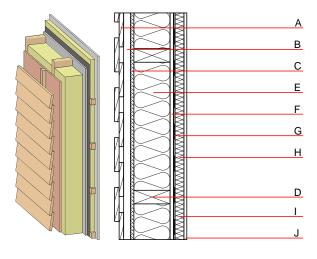

Note: e=400

## Register of building materials used for this application, cross-section (from outside to inside, dimensions in mm)

	Thickness	hickness Building material Thermal performance					Reaction to fire	
			λ	μ min – max	ρ	С	EN	
Α	24.0	larch wood external wall cladding	0.155	150	600	1.600	D	
В	30.0	spruce wood battens offset (30/50; 30/80) - ventilation	0.120	50	450	1.600	D	
С	15.0	fibreboard (MDF)	0.140	11	600	1.700	D	
D	160.0	construction timber (60/; e=*)	0.120	50	450	1.600	D	
E	160.0	mineral wool [040; ≥16; <1000°C]	0.040	1	16	1.030	A1	
F	15.0	gypsum fibre board	0.320	21	1000	1.100	A2	
G		vapour barrier sd≥ 1 m			1000			
Н	40.0	spruce wood cross battens (a=400) or battens offset)	0.120	50	450	1.600	D	
I	40.0	mineral wool [040; ≥16; <1000°C] or air layer in type 02	0.040	1	16	1.030	A1	
J	12.5	gypsum fibre board or	0.320	21	1000	1.100	A2	
J	12.5	gypsum plaster board type DF	0.250	10	800	1.050	A2	

# Sustainability rating (per m<sup>2</sup>) Database ecoinvent 23.7 $013_{Kon}$



Designation: awrhhi03a-11 8/2/23 Holzforschung Austria Last updated:

Source:

Editor: HFA, SP

### Details of sustainability rating

#### Database ecoinvent

Lifecycle	GWP	AP	EP	ODP	POCP	
(Phases)	[kg CO <sub>2</sub> -e.]	[kg SO <sub>2</sub> -e.]	[kg PO <sub>4</sub> -e.]	[kg R11-e.]	[kg Ethen-e.]	
A1 - A3		0.115	0.052	2,12E-6	0.023	
	,		,	'	'	1
Lifecycle	PERE	PERM	PERT	PENRE	PENRM	PENRT
(Phases)	[MJ]	[MJ]	[MJ]	[MJ]	[MJ]	[MJ]
A1 - A3	109.225	629.684	738.909	406.689	30.791	437.480