

Designation: awrhhi03a-05 Last updated: 8/2/23

Holzforschung Austria Source:

Editor: HFA, SP

External wall - awrhhi03a-05

external wall, timber frame construction, ventilated, with dry lining, with cladding, other surface

Performance rating


REI from inside 60 Fire protection performance REI from outside 30 maximum ceiling height = 3 m; maximum load $E_{d,fi}$ = 19,2 kN/m Classified by HFA

Thermal performance Calculated by HFA	U Diffusion	0.16 W/(m²K) suitable
Acoustic performance	R _w (C;C _{tr}) L _{n,w} (C _I)	51(-3;-10) dB

Battens for the ventilation space screwed onto the structural timber together with vertical battens for the dry lining screwed directly onto the ledger beams will result in Rw(C;Ctr)=44(-1;-5) dB Assessed by MA39

Mass per unit area 52.70 kg/m^2

Calculation based on GF

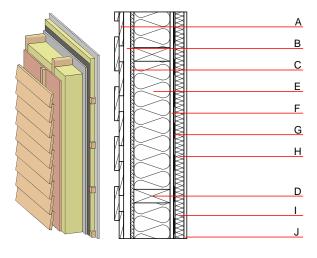

Note: e=625

Register of building materials used for this application, cross-section (from outside to inside, dimensions in mm)

	Thickness	Building material	Thermal pe	rformance			Reaction to fire
			λ	μ min – max	ρ	С	EN
Α	24.0	larch wood external wall cladding	0.155	150	600	1.600	D
В	30.0	spruce wood battens offset (30/50; 30/80) - ventilation	0.120	50	450	1.600	D
С	15.0	fibreboard (MDF)	0.140	11	600	1.700	D
D	200.0	construction timber (60/; e=*)	0.120	50	450	1.600	D
E	200.0	mineral wool [040; ≥16; <1000°C]	0.040	1	16	1.030	A1
F	15.0	gypsum fibre board	0.320	21	1000	1.100	A2
G		vapour barrier sd≥ 1 m			1000		
Н	80.0	spruce wood cross battens (a=400) or battens offset)	0.120	50	450	1.600	D
I	80.0	mineral wool [040; ≥16; <1000°C] or air layer in type 02	0.040	1	16	1.030	A1
J	12.5	gypsum fibre board or	0.320	21	1000	1.100	A2
J	12.5	gypsum plaster board type DF	0.250	10	800	1.050	A2

Sustainability rating (per m²) Database ecoinvent 29.1 Calculated by HFA



Designation: awrhhi03a-05 8/2/23 Holzforschung Austria Last updated:

Source:

HFA, SP Editor:

Details of sustainability rating

Database ecoinvent

Lifecycle	GWP	AP	EP	ODP	POCP	
(Phases)	[kg CO ₂ -e.]	[kg SO ₂ -e.]	[kg PO ₄ -e.]	[kg R11-e.]	[kg Ethen-e.]	
A1 - A3		0.136	0.061	2,49E-6	0.026	
	1	1		1	1	
Lifecycle	PERE	PERM	PERT	PENRE	PENRM	PENRT
Lifecycle (Phases)	PERE [MJ]	[MJ]	PERT [MJ]	PENRE [MJ]	PENRM [MJ]	PENRT [MJ]