

External wall - awrhh04a-15

external wall, timber frame construction, ventilated, with dry lining, with cladding, other surface

Performance rating

Fire protection performance REI from inside 60
REI from outside 30
maximum ceiling height = 3 m; maximum load $E_{d,fi} = 19,2 \text{ kN/m}$
Classified by HFA
Classified by HFA

Germany

F60 (from inside)/F30 (from outside)
Load $E_{d,fi}$ according to the German certification document
Corresponding proof: manufacturer-specific

Thermal performance U 0.18 W/(m²K)
Diffusion suitable


Calculated by TUM

Acoustic performance $R_w (C; C_{tr})$ 51 (-3; 10) dB
 $L_{n,w} (C_i)$

Assessed by Müller-BBM

Mass per unit area m 64.40 kg/m²

Calculation based on gypsum plaster board type DF

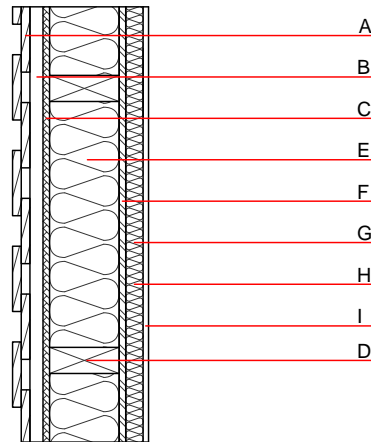

Note: dry lining $\geq 40 \text{ mm}$

Register of building materials used for this application, cross-section (from outside to inside, dimensions in mm)

| | Thickness | Building material | Thermal performance | | | | Reaction to fire | |
|---|-----------|---|---------------------|--------------------------------|--------|-------|------------------|--|
| | | | λ | $\mu \text{ min} - \text{max}$ | ρ | c | EN | |
| A | 24.0 | larch wood external wall cladding | 0.155 | 150 | 600 | 1.600 | D | |
| B | 30.0 | spruce wood battens offset (30/50; 30/80) - ventilation | 0.120 | 50 | 450 | 1.600 | D | |
| C | 15.0 | fibreboard (MDF) | 0.140 | 11 | 600 | 1.700 | D | |
| D | 200.0 | construction timber (60/..; e=625) | 0.120 | 50 | 450 | 1.600 | D | |
| E | 200.0 | Wood fibre insulation [039; 45] | 0.039 | 1 - 2 | 45 | 2.100 | E | |
| F | 15.0 | OSB | 0.130 | 200 | 600 | 1.700 | D | |
| G | 40.0 | spruce wood cross battens (a=400) $\geq 40\text{mm}$ | 0.120 | 50 | 450 | 1.600 | D | |
| H | 40.0 | Wood fibre insulation [039; 45] | 0.039 | 1 - 2 | 45 | 2.100 | E | |
| I | 12.5 | gypsum plaster board type DF or | 0.250 | 10 | 800 | 1.050 | A2 | |
| I | 12.5 | gypsum fibre board | 0.320 | 21 | 1000 | 1.100 | A2 | |

Sustainability rating (per m²)

Database ecoinvent

O13_{Kon} 19.4

Calculated by HFA

Database GaBi (ÖKOBAUDAT)

Built-in renewable materials kg 59.430
Biogenic carbon in kg CO₂-e. kg CO₂ 86.080
Energy use of Primary Energy MJ 1192.180
Share of renewable PE % 38.34

Calculated by TUM

Details of sustainability rating

Database ecoinvent

| Lifecycle (Phases) | GWP [kg CO ₂ -e.] | AP [kg SO ₂ -e.] | EP [kg PO ₄ -e.] | ODP [kg R11-e.] | POCP [kg Ethen-e.] | |
|-----------------------|---------------------------------|--------------------------------|--------------------------------|--------------------|-----------------------|--|
| A1 - A3 | | 0.113 | 0.049 | 1,94E-6 | 0.025 | |

| Lifecycle (Phases) | PERE [MJ] | PERM [MJ] | PERT [MJ] | PENRE [MJ] | PENRM [MJ] | PENRT [MJ] |
|-----------------------|--------------|--------------|--------------|---------------|---------------|---------------|
| A1 - A3 | 141.023 | 913.031 | 1054.054 | 401.932 | 45.530 | 447.462 |

Database GaBi (ÖKOBAUDAT)

| Lifecycle (Phases) | GWP [kg CO ₂ -e.] | AP [kg SO ₂ -e.] | EP [kg PO ₄ -e.] | ODP [kg R11-e.] | POCP [kg Ethen-e.] | |
|-----------------------|---------------------------------|--------------------------------|--------------------------------|--------------------|-----------------------|--|
| A1 - A3 | | 0.134 | 0.029 | 1,64E-6 | 0.038 | |
| C1 - C4 | | 0.002 | 0.000 | 1,06E-7 | 0.000 | |
| A1 - C4 | | 0.138 | 0.030 | 1,75E-6 | 0.038 | |

| Lifecycle (Phases) | PERE [MJ] | PERM [MJ] | PERT [MJ] | PENRE [MJ] | PENRM [MJ] | PENRT [MJ] |
|-----------------------|--------------|--------------|--------------|---------------|---------------|---------------|
| A1 - A3 | 454.503 | 1377.220 | 1831.729 | 702.255 | 63.360 | 765.710 |
| C1 - C4 | 2.204 | -1372.966 | -1370.762 | 27.612 | -62.418 | -34.810 |
| A1 - C4 | 457.086 | 4.513 | 461.605 | 735.097 | 0.994 | 736.180 |