

Designation: awrhhi04a-04 Last updated: 8/2/23

Source: Holzforschung Austria

Editor: HFA, SP

### External wall - awrhhi04a-04

external wall, timber frame construction, ventilated, with dry lining, with cladding, other surface

#### Performance rating

 $\begin{tabular}{lll} Fire protection & REI from inside & 60 \\ performance & REI from outside & 30 \\ \hline maximum ceiling height = 3 m; maximum load $E_{d,fi}$ = 19,2 kN/m \\ Classified by MA39 \\ Classified by HFA & & & \\ \hline \end{tabular}$ 


Thermal performance  Calculated by HFA	U Diffusion	0.16 W/(m <sup>2</sup> K) suitable	
Acoustic performance	R <sub>w</sub> (C;C <sub>tr</sub> ) L <sub>n w</sub> (C <sub>l</sub> )	52(-3;-10) dB	

Battens for the ventilation space screwed onto the structural timber together with vertical battens for the dry lining screwed directly onto the ledger beams will result in Rw(C;Ctr)=45(-1;-5) Assessed by MA39

\_\_\_\_\_

 $\label{eq:mass_per_unit_area} \mbox{Mass per unit area} \qquad \mbox{m} \qquad \qquad 46.80 \mbox{ kg/m}^2$ 

Calculation based on gypsum plaster board type DF

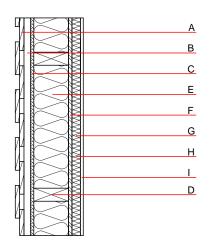

# Register of building materials used for this application, cross-section (from outside to inside, dimensions in mm)

	Thickness	Building material Thermal performance					Reaction to fire	
			λ	μ min – max	ρ	С	EN	
Α	24.0	larch wood external wall cladding	0.155	150	600	1.600	D	
В	30.0	spruce wood battens offset (30/50; 30/80) - ventilation	0.120	50	450	1.600	D	
С	15.0	fibreboard (MDF)	0.140	11	600	1.700	D	
D	240.0	construction timber (60/; e=625)	0.120	50	450	1.600	D	
E	240.0	mineral wool [040; ≥16; <1000°C]	0.040	1	16	1.030	A1	
F	15.0	OSB	0.130	200	600	1.700	D	
G	40.0	spruce wood cross battens (a=400) resp. battens offset	0.120	50	450	1.600	D	
Н	40.0	mineral wool [040; ≥16; <1000°C]	0.040	1	16	1.030	A1	
1	12.5	gypsum plaster board type DF or	0.250	10	800	1.050	A2	
1	12.5	gypsum fibre board	0.320	21	1000	1.100	A2	

## Sustainability rating (per m²)

Database ecoinvent
OI3<sub>Kon</sub> 28.3

Calculated by HFA



Designation: awrhhi04a-04 Last updated:

8/2/23 Holzforschung Austria Source:

HFA, SP Editor:

### Details of sustainability rating

#### Database ecoinvent

Lifecycle	GWP	AP	EP	ODP	POCP	
(Phases)	[kg CO <sub>2</sub> -e.]	[kg SO <sub>2</sub> -e.]	[kg PO <sub>4</sub> -e.]	[kg R11-e.]	[kg Ethen-e.]	
A1 - A3		0.146	0.065	2,43E-6	0.028	
Lifecycle	PERE	PERM	PERT	PENRE	PENRM	PENRT
(Phases)	[MJ]	[MI]	[MJ]	[MJ]	[MJ]	[MJ]
A1 - A3	136.304	768.336	904.640	473.077	28.891	501.968