

Designation: awrhhi05a-04 8/2/23 Last updated:

Holzforschung Austria Source:

Editor: HFA, SP

## External wall - awrhhi05a-04

external wall, timber frame construction, ventilated, with dry lining, with cladding, other surface

## Performance rating


**REI** from inside 60 Fire protection performance REI from outside 30 maximum ceiling height = 3 m; maximum load  $E_{d,fi}$  = 19,2 kN/m Classified by HFA

Thermal performance	U Diffusion	0.16 W/(m <sup>2</sup> K) suitable
Calculated by HFA		
Acoustic performance	R <sub>w</sub> (C;C <sub>tr</sub> ) L <sub>n,w</sub> (C <sub>l</sub> )	52(-3;-10) dB
Battens for the ventilation	space screwed onto	the structural timber together with

vertical battens for the dry lining screwed directly onto the ledger beams will result in Rw(C;Ctr)=45(-1;-5) Assessed by MA39

Mass per unit area  $45.70~\text{kg/m}^2$ 

Calculation based on gypsum plaster board type DF

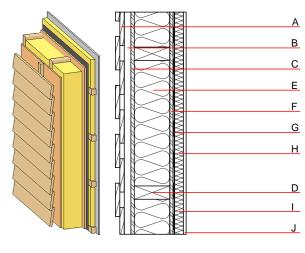

Note: e=625

## Register of building materials used for this application, cross-section (from outside to inside, dimensions in mm)

	Thickness	Building material	Thermal performance				Reaction to fire
			λ	μ min – max	ρ	С	EN
Α	24.0	larch wood external wall cladding	0.155	150	600	1.600	D
В	30.0	spruce wood battens offset (30/50; 30/80) - ventilation	0.120	50	450	1.600	D
С	15.0	OSB	0.130	200	600	1.700	D
D	240.0	construction timber (60/; e=*)	0.120	50	450	1.600	D
E	240.0	mineral wool [040; ≥16; <1000°C]	0.040	1	16	1.030	A1
F	15.0	OSB	0.130	200	600	1.700	D
G		vapour barrier sd≥ 10m			1000		
Н	40.0	spruce wood cross battens (a=400) or battens offset)	0.120	50	450	1.600	D
I	40.0	mineral wool [040; ≥16; <1000°C]	0.040	1	16	1.030	A1
J	12.5	gypsum plaster board type DF or	0.250	10	800	1.050	A2
J	12.5	gypsum fibre board	0.320	21	1000	1.100	A2

# Sustainability rating (per m<sup>2</sup>) Database ecoinvent 27.6 $013_{Kon}$ Calculated by HFA



Designation: awrhhi05a-04 8/2/23 Holzforschung Austria Last updated:

Source:

HFA, SP Editor:

### Details of sustainability rating

#### Database ecoinvent

Lifecycle	GWP	AP	EP	ODP	POCP	
(Phases)	[kg CO <sub>2</sub> -e.]	[kg SO <sub>2</sub> -e.]	[kg PO <sub>4</sub> -e.]	[kg R11-e.]	[kg Ethen-e.]	
A1 - A3		0.142	0.062	2,51E-6	0.029	
Lifecycle	PERE	PERM	PERT	PENRE	PENRM	PENRT
Lifecycle (Phases)	PERE [MJ]	PERM [MJ]	PERT [MJ]	PENRE [MJ]	PENRM [MJ]	PENRT [MJ]