

Designation: awrhhi05a-07 Last updated: 8/2/23

Holzforschung Austria Source:

Editor: HFA, SP

External wall - awrhhi05a-07

external wall, timber frame construction, ventilated, with dry lining, with cladding, other surface

Performance rating

REI from inside 60 Fire protection performance REI from outside 30 maximum ceiling height = 3 m; maximum load $E_{d,fi}$ = 19,2 kN/m Classified by HFA


Thermal performance	U Diffusion	$0.19 \text{ W/(m}^2\text{K)}$ suitable
Calculated by HFA		
Acoustic performance	R _w (C;C _{tr}) L _{n,w} (C _I)	51(-3;-10) dB

Battens for the ventilation space screwed onto the structural timber together with vertical battens for the dry lining screwed directly onto the ledger beams will result in Rw(C;Ctr)=44(-1;-5)

Assessed by MA39

Mass per unit area $46.80~\text{kg/m}^2$

Calculation based on gypsum plaster board type DF

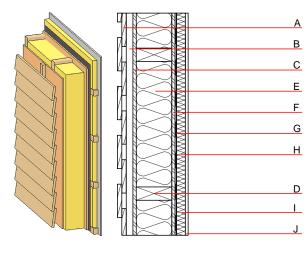

Note: e=625

Register of building materials used for this application, cross-section (from outside to inside, dimensions in mm)

	Thickness	ss Building material Thermal performance					Reaction to fire
			λ	μ min – max	ρ	С	EN
Α	24.0	larch wood external wall cladding	0.155	150	600	1.600	D
В	30.0	spruce wood battens offset (30/50; 30/80) - ventilation	0.120	50	450	1.600	D
С	15.0	OSB	0.130	200	600	1.700	D
D	160.0	construction timber (60/; e=*)	0.120	50	450	1.600	D
Е	160.0	mineral wool [035; 50; <1000°C]	0.035	1	50	1.030	A1
F	15.0	OSB	0.130	200	600	1.700	D
G		vapour barrier sd≥ 10m			1000		
Н	40.0	spruce wood cross battens (a=400) or battens offset)	0.120	50	450	1.600	D
Ι	40.0	mineral wool [035; 50; <1000°C]	0.035	1	50	1.030	A1
J	12.5	gypsum plaster board type DF or	0.250	10	800	1.050	A2
J	12.5	gypsum fibre board	0.320	21	1000	1.100	A2

Sustainability rating (per m²)

Database ecoinvent

OI3_{Kon} 44.7

Calculated by HFA



Designation: awrhhi05a-07 Last updated:

8/2/23 Holzforschung Austria Source:

HFA, SP Editor:

Details of sustainability rating

Database ecoinvent

Lifecycle	GWP	AP	EP	ODP	POCP	
(Phases)	[kg CO ₂ -e.]	[kg SO ₂ -e.]	[kg PO ₄ -e.]	[kg R11-e.]	[kg Ethen-e.]	
A1 - A3		0.203	0.090	3,59E-6	0.035	
Lifecycle	PERE	PERM	PERT	PENRE	PENRM	PENRT
(Phases)	[MJ]	[MJ]	[MJ]	[MJ]	[MJ]	[MJ]
A1 - A3	144.075	675.519	819.594	651.896	23.973	675.869