

External wall - awrhi06a-04

external wall, timber frame construction, ventilated, with dry lining, with cladding, other surface

Performance rating

Fire protection performance	REI from inside	60
	REI from outside	30
maximum ceiling height = 3 m; maximum load $E_{d,fi}$ = 19,2 kN/m		
Classified by HFA		

Thermal performance	U	0.15 W/(m ² K)
	Diffusion	suitable

Calculated by HFA


Acoustic performance	R_w (C;C _{tr})	52(-3;-10) dB
	$L_{n,w}$ (C _i)	

Battens for the ventilation space screwed onto the structural timber together with vertical battens for the dry lining screwed directly onto the ledger beams will result in $R_w(C;C_{tr})=45(-2;-5)$

Assessed by MA39

Mass per unit area	m	54.40 kg/m ²
--------------------	---	-------------------------

Calculation based on gypsum plaster board type DF

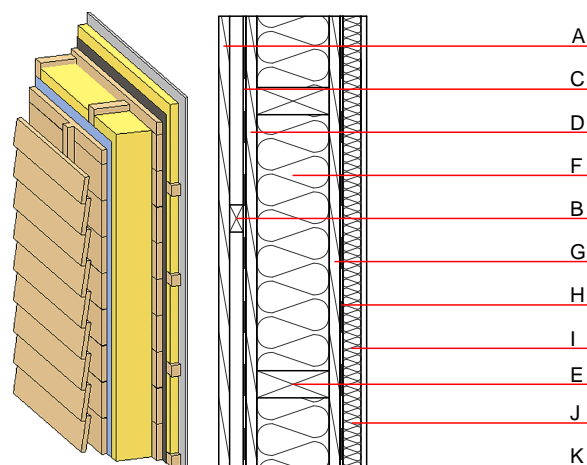

Note: e=625

Register of building materials used for this application, cross-section (from outside to inside, dimensions in mm)

	Thickness	Building material	Thermal performance				Reaction to fire EN
			λ	μ min – max	ρ	c	
A	24.0	larch wood external wall cladding	0.155	150	600	1.600	D
B	30.0	spruce wood battens offset (30/50; 30/80) - ventilation	0.120	50	450	1.600	D
C		wind barrier			1000		
D	25.0	planking spruce wood	0.120	50	450	1.600	D
E	240.0	construction timber (60/..; e=*)	0.120	50	450	1.600	D
F	240.0	mineral wool [040; ≥ 16 ; <1000°C]	0.040	1	16	1.030	A1
G	25.0	planking spruce wood	0.120	50	450	1.600	D
H		vapour barrier sd ≥ 5 m			1000		
I	40.0	spruce wood cross battens (a=400) or battens offset)	0.120	50	450	1.600	D
J	40.0	mineral wool [040; ≥ 16 ; <1000°C]	0.040	1	16	1.030	A1
K	12.5	gypsum plaster board type DF or	0.250	10	800	1.050	A2
K	12.5	gypsum fibre board	0.320	21	1000	1.100	A2

Sustainability rating (per m²)

Database ecoinvent

OL3 _{Kon}	23.0
--------------------	------

Calculated by HFA

Details of sustainability rating

Database ecoinvent

Lifecycle (Phases)	GWP [kg CO ₂ -e.]	AP [kg SO ₂ -e.]	EP [kg PO ₄ -e.]	ODP [kg R11-e.]	POCP [kg Ethen-e.]	
A1 - A3		0.140	0.063	2,43E-6	0.009	
Lifecycle (Phases)	PERE [MJ]	PERM [MJ]	PERT [MJ]	PENRE [MJ]	PENRM [MJ]	PENRT [MJ]
A1 - A3	61.705	894.026	955.731	430.898	12.604	443.503