

Designation: awrhhi06a-08 Last updated: 8/2/23

Holzforschung Austria Source:

Editor: HFA, SP

# External wall - awrhhi06a-08

external wall, timber frame construction, ventilated, with dry lining, with cladding, other surface

### Performance rating

**REI** from inside 60 Fire protection performance REI from outside 30 maximum ceiling height = 3 m; maximum load  $E_{d,fi}$  = 19,2 kN/m Classified by HFA


Thermal performance	U Diffusion	0.20 W/(m <sup>2</sup> K) suitable
Calculated by HFA		
Acoustic performance	R <sub>w</sub> (C;C <sub>tr</sub> ) L <sub>n,w</sub> (C <sub>I</sub> )	51(-3;-10) dB

Battens for the ventilation space screwed onto the structural timber together with vertical battens for the dry lining screwed directly onto the ledger beams will result in Rw(C;Ctr)=44(-2;-5)

Assessed by MA39

Mass per unit area  $52.50 \text{ kg/m}^2$ 

Calculation based on gypsum plaster board type DF

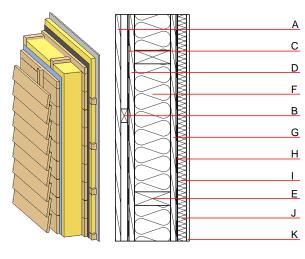

Note: e=625

# Register of building materials used for this application, cross-section (from outside to inside, dimensions in mm)

	Thickness	Building material	Thermal performance				Reaction to fire
			λ	μ min – max	ρ	С	EN
Α	24.0	larch wood external wall cladding	0.155	150	600	1.600	D
В	30.0	spruce wood battens offset (30/50; 30/80) - ventilation	0.120	50	450	1.600	D
С		wind barrier			1000		
D	25.0	planking spruce wood	0.120	50	450	1.600	D
Е	160.0	construction timber (60/; e=*)	0.120	50	450	1.600	D
F	160.0	mineral wool [038; ≥33; ≥1000°C]	0.038	1	33	1.030	A1
G	25.0	planking spruce wood	0.120	50	450	1.600	D
Н		vapour barrier sd≥ 5m			1000		
I	40.0	spruce wood cross battens (a=400) or battens offset)	0.120	50	450	1.600	D
J	40.0	mineral wool [038; ≥33; ≥1000°C]	0.038	1	33	1.030	A1
K	12.5	gypsum plaster board type DF or	0.250	10	800	1.050	A2
K	12.5	gypsum fibre board	0.320	21	1000	1.100	A2

# Sustainability rating (per m<sup>2</sup>) Database ecoinvent OI3<sub>Kon</sub> 25.7 Calculated by HFA



Designation: awrhhi06a-08 8/2/23 Holzforschung Austria Last updated:

Source:

HFA, SP Editor:

### Details of sustainability rating

#### Database ecoinvent

Lifecycle	GWP	AP	EP	ODP	POCP	
(Phases)	[kg CO <sub>2</sub> -e.]	[kg SO <sub>2</sub> -e.]	[kg PO <sub>4</sub> -e.]	[kg R11-e.]	[kg Ethen-e.]	
A1 - A3		0.167	0.053	1,69E-6	0.035	
Lifecycle	PERE	PERM	PERT	PENRE	PENRM	PENRT
(Phases)	[MJ]	[MJ]	[MJ]	[MJ]	[MJ]	[MJ]
A1 - A3	53.468	830.916	884.383	361.536	12.604	374.141