

Designation: awrhhi08b-11 8/2/23 Last updated:

Holzforschung Austria Source:

Editor: HFA, SP

## External wall - awrhhi08b-11

external wall, timber frame construction, ventilated, with dry lining, with cladding, other surface

### Performance rating


**REI** from inside 60 Fire protection performance RFI from outside 60 maximum ceiling height = 3 m; maximum load  $E_{d,fi}$  = 19,2 kN/m Classified by HFA

Thermal performance	U Diffusion	0.23 W/(m <sup>2</sup> K) suitable					
Calculated by HFA							
Acoustic performance	R <sub>w</sub> (C;C <sub>tr</sub> ) L <sub>n,w</sub> (C <sub>l</sub> )	52(-2;-8) dB					
Pattons for the ventilation space servined anto the structural timber together with							

Battens for the ventilation space screwed onto the structural timber together with vertical battens for the dry lining screwed directly onto the ledger beams will result in Rw(C;Ctr)=45(-1;-5) dB Assessed by MA39

Mass per unit area  $62.10 \text{ kg/m}^2$ 

Calculation based on GF

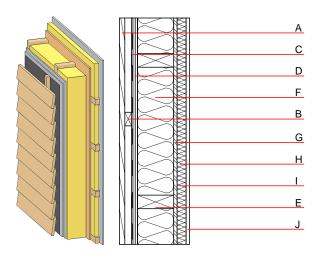

Note: e=400

## Register of building materials used for this application, cross-section (from outside to inside, dimensions in mm)

	Thickness	Building material	Thermal per	Thermal performance			
		λ	μ min – max	ρ	С	EN	
A	24.0	larch wood external wall cladding	0.155	150	600	1.600	D
В	30.0	spruce wood battens offset (30/50; 30/80) - ventilation	0.120	50	450	1.600	D
С		wind barrier			1000		
D	20.0	gypsum fibre board (2x10 mm)	0.320	21	1000	1.100	A2
E	160.0	mineral wool [040; ≥16; <1000°C]	0.040	1	16	1.030	A1
F	160.0	construction timber (60; e=*)	0.120	50	450	1.600	D
G	15.0	OSB (sealed with airtight tape)	0.130	200	600	1.700	D
Н	40.0	spruce wood cross battens (a=400) or battens offset)	0.120	50	450	1.600	D
	40.0	mineral wool [040; ≥16; <1000°C] or air layer in type 02	0.040	1	16	1.030	A1
	15.0	gypsum fibre board or	0.320	21	1000	1.100	A2
J	15.0	gypsum plaster board type DF	0.250	10	800	1.050	A2

# Sustainability rating (per m<sup>2</sup>)

Database ecoinvent 26.5 OI3<sub>Kon</sub>

Calculated by HFA



Designation: awrhhi08b-11 8/2/23 Holzforschung Austria Last updated:

Source:

HFA, SP Editor:

### Details of sustainability rating

#### Database ecoinvent

Lifecycle	GWP	AP	EP	ODP	POCP	
(Phases)	[kg CO <sub>2</sub> -e.]	[kg SO <sub>2</sub> -e.]	[kg PO <sub>4</sub> -e.]	[kg R11-e.]	[kg Ethen-e.]	
A1 - A3		0.128	0.057	2,64E-6	0.008	
Lifecycle	PERE	PERM	PERT	PENRE	PENRM	PENRT
(Phases)	[MJ]	[MJ]	[MJ]	[MJ]	[MJ]	[MJ]
A1 - A3	103.016	638.916	741.932	453.487	19.334	472.822