

Designation: awrhhi09a-04 Last updated: 8/2/23

Source: Holzforschung Austria

Editor: HFA, PLB


# External wall - awrhhi09a-04

external wall, timber frame construction, ventilated, with dry lining, with cladding, wooden surface

## Performance rating

 $\begin{array}{cccc} \textbf{Fire protection} & \textbf{REI from inside} & 30 \\ \textbf{performance} & \textbf{REI from outside} & 30 \\ \\ \textbf{maximum ceiling height} = 3 \text{ m; maximum load } E_{d,fi} = 32 \text{ kN/m} \\ \\ \textbf{Classified by HFA} \\ \end{array}$ 

Thermal performance	U Diffusion	0.15 W/(m <sup>2</sup> K) suitable
Calculated by HFA		
Acoustic performance	R <sub>w</sub> (C;C <sub>tr</sub> ) L <sub>n,w</sub> (C <sub>I</sub> )	46(-2;-6) dB
with closed wooden facac	le R <sub>w</sub> von 50 (-3; -9)	
Assessed by TGM		
Mass per unit area	m	66.20 kg/m <sup>2</sup>

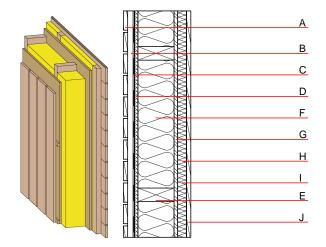

## Register of building materials used for this application, cross-section (from outside to inside, dimensions in mm)

	Thickness	Building material	Thermal per	Thermal performance			
			λ	μ min – max	ρ	С	EN
Α	19.0	larch wood external wall cladding (open) vertical	0.155	150	600	1.600	D
В	30.0	larch wood - cross battens (30/50; 30/80) - ventilation	0.155	150	600	1.600	D
С		wind barrier			1000		
D	15.0	fibreboard (MDF)	0.140	11	600	1.700	D
Ε	240.0	construction timber (60/; e=625)	0.120	50	450	1.600	D
F	240.0	Cellulose fibre [040; 50]	0.040	1	50	2.000	E
G	15.0	OSB	0.130	200	600	1.700	D
Н	40.0	spruce wood cross battens (a=400) or battens offset)	0.120	50	450	1.600	D
I	40.0	Cellulose fibre [040; 50]	0.040	1	50	2.000	E
J	19.0	planking tongue and groove	0.120	50	450	1.600	D

### Sustainability rating (per m<sup>2</sup>)

Database ecoinvent

**OI3**<sub>Kon</sub> 21.8

Calculated by IBO



Designation: awrhhi09a-04 Last updated:

8/2/23 Holzforschung Austria Source:

HFA, PLB Editor:

### Details of sustainability rating

#### Database ecoinvent

Lifecycle	GWP	AP	EP	ODP	POCP	
(Phases)	[kg CO <sub>2</sub> -e.]	[kg SO <sub>2</sub> -e.]	[kg PO <sub>4</sub> -e.]	[kg R11-e.]	[kg Ethen-e.]	
A1 - A3		0.156	0.059	1.88E-6	0.008	
Lifecycle	PERE	PERM	PERT	PENRE	PENRM	PENRT
(Phases)	[MJ]	[MJ]	[MJ]	[MJ]	[MJ]	[MJ]