

Designation: awrhho01a-03 Last updated: 8/2/23

Holzforschung Austria Source:

Editor: HFA, PLB

## External wall - awrhho01 a-03

external wall, timber frame construction, ventilated, without dry lining, with cladding, other surface


### Performance rating

**REI** from inside 60 Fire protection performance REI from outside 30 maximum ceiling height = 3 m; maximum load  $E_{d,fi}$  = 32,0 kN/m Classified by MA39

Classified by HFA		
Thermal performance	U Diffusion	0.18 W/(m <sup>2</sup> K) suitable
Calculated by HFA		
Acoustic performance	R <sub>w</sub> (C;C <sub>tr</sub> ) L <sub>n,w</sub> (C <sub>l</sub> )	49(-2;-8) dB
Battens for the ventilation Rw(C;Ctr)=45(-1;-7) dB Assessed by MA39	n space screwed onto	the structural timber result in an

Mass per unit area  $43.70~\text{kg/m}^2$ 

Calculation based on gypsum plaster board type DF

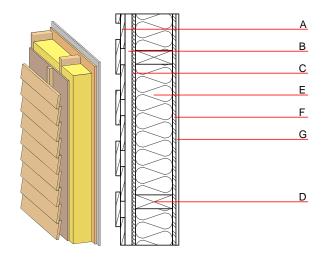

## Register of building materials used for this application, cross-section (from outside to inside, dimensions in mm)

	Thickness	Building material	Thermal per	formance			Reaction to fire
			λ	μ min – max	ρ	С	EN
Α	24.0	larch wood external wall cladding	0.155	150	600	1.600	D
В	30.0	spruce wood battens offset (30/50; 30/80) - ventilation	0.120	50	450	1.600	D
С	15.0	fibreboard (MDF)	0.140	11	600	1.700	D
D	240.0	construction timber (60/; e=625)	0.120	50	450	1.600	D
E	240.0	mineral wool [040; ≥16; <1000°C]	0.040	1	16	1.030	A1
F	15.0	OSB (sealed with airtight tape)	0.130	200	600	1.700	D
G	12.5	gypsum plaster board type DF or	0.250	10	800	1.050	A2
G	12.5	gypsum fibre board	0.320	21	1000	1.100	A2

# Sustainability rating (per m<sup>2</sup>) Database ecoinvent OI3<sub>Kon</sub> 26.0

Calculated by HFA



Designation: awrhho01a-03 Last updated:

8/2/23 Holzforschung Austria Source:

HFA, PLB Editor:

### Details of sustainability rating

#### Database ecoinvent

	Í.	1	1	1	i i	1
Lifecycle	GWP	AP	EP	ODP	POCP	
(Phases)	[kg CO <sub>2</sub> -e.]	[kg SO <sub>2</sub> -e.]	[kg PO <sub>4</sub> -e.]	[kg R11-e.]	[kg Ethen-e.]	
A1 - A3		0.134	0.059	2,23E-6	0.026	
Lifecycle	PERE	PERM	PERT	PENRE	PENRM	PENRT
(Phases)	[MJ]	[MJ]	[MJ]	[MI]	[MJ]	[MJ]
A1 - A3	127.617	719.202	846.820	437.918	28.891	466.810