

## External wall - awrho05b-01

external wall, timber frame construction, ventilated, without dry lining, with cladding, other surface

### Performance rating

Fire protection performance	REI from inside	60
	REI from outside	30

maximum ceiling height = 3 m; maximum load  $E_{d,fi}$  = 25,0 kN/m  
 Classified by HFA

Thermal performance	U	0.34 W/(m <sup>2</sup> K)
	Diffusion	suitable


Calculated by HFA

Acoustic performance	$R_w$ (C;C <sub>tr</sub> )	44(-2;-8) dB
	$L_{n,w}$ (C <sub>i</sub> )	

Battens for the ventilation space screwed onto the structural timber result in an  $R_w(C;C_{tr})=40(-1;-7)$  dB  
 Assessed by MA39

Mass per unit area	m	26.60 kg/m <sup>2</sup>
--------------------	---	-------------------------

Calculation based on GF

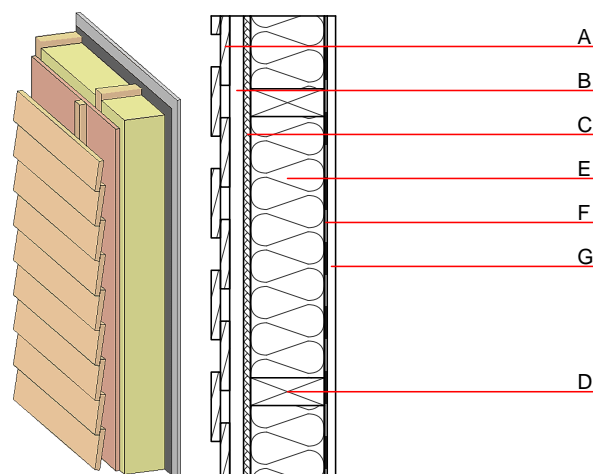

Note: e=625

### Register of building materials used for this application, cross-section (from outside to inside, dimensions in mm)

	Thickness	Building material	Thermal performance				Reaction to fire EN
			$\lambda$	$\mu$ min – max	$\rho$	c	
A	24.0	larch wood external wall cladding	0.155	150	600	1.600	D
B	30.0	spruce wood battens offset (30/50; 30/80) - ventilation	0.120	50	450	1.600	D
C	15.0	fibreboard (MDF)	0.140	11	600	1.700	D
D	120.0	construction timber (60/...; e=*)	0.120	50	450	1.600	D
E	120.0	mineral wool [040; ≥16; <1000°C]	0.040	1	16	1.030	A1
F		vapour barrier sd≥ 1m			1000		
G	18.0	gypsum fibre board or	0.320	21	1000	1.100	A2
G	18.0	gypsum plaster board type DF	0.250	10	800	1.050	A2

### Sustainability rating (per m<sup>2</sup>)

#### Database ecoinvent

013 <sub>Kon</sub>	17.1
--------------------	------

Calculated by HFA

## Details of sustainability rating

### Database ecoinvent

Lifecycle (Phases)	GWP [kg CO <sub>2</sub> -e.]	AP [kg SO <sub>2</sub> -e.]	EP [kg PO <sub>4</sub> -e.]	ODP [kg R11-e.]	POCP [kg Ethen-e.]	
A1 - A3		0.085	0.038	1,49E-6	0.016	

Lifecycle (Phases)	PERE [MJ]	PERM [MJ]	PERT [MJ]	PENRE [MJ]	PENRM [MJ]	PENRT [MJ]
A1 - A3	93.518	478.351	571.869	298.240	22.510	320.750