

Designation: awrhho07a-14 Last updated: 8/2/23

Holzforschung Austria Source:

Editor: HFA, SP

External wall - awrhho07a-14


external wall, timber frame construction, ventilated, without dry lining, with cladding, other surface

Performance rating

REI from inside 60 Fire protection performance REI from outside 30 maximum ceiling height = 3 m; maximum load $E_{d,fi}$ = 32,0 kN/m Classified by HFA Classified by HFA

| Thermal performance | U Diffusion | 0.14 W/(m ² K) suitable |
|----------------------|---|---------------------------------------|
| Acoustic performance | R_w (C;C _{tr}) $L_{n,w}$ (C _l) | 48(-2;-8) dB |
| Mass per unit area | m | 66 50 kg/m² |

Calculation based on gypsum plaster board type DF

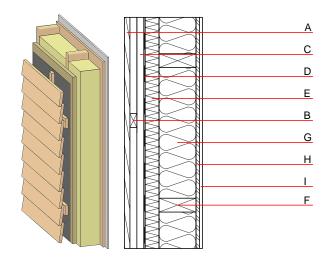

Note: According to OIB-RL 2 (Austria) is for ventilated and insulated facades (from building class 2) an insulation material with minimum Euroclass D

Register of building materials used for this application, cross-section (from outside to inside, dimensions in mm)

| | Thickness | Building material | Thermal pe | rformance | | | Reaction to fire |
|---|-----------|--|------------|-------------|------|-------|------------------|
| | | | λ | μ min – max | ρ | С | EN |
| Α | 24.0 | larch wood external wall cladding | 0.155 | 150 | 600 | 1.600 | D |
| В | 30.0 | spruce wood battens - ventilation | 0.120 | 50 | 450 | 1.600 | D |
| С | 30.0 | spruce wood cross battens | 0.120 | 50 | 450 | 1.600 | D |
| D | | wind barrier | | | 1000 | | |
| E | 60.0 | wood-fibre insulation board [045; 140] | 0.045 | 2 - 5 | 140 | 2.100 | Е |
| F | 240.0 | construction timber (60/; e=625) | 0.120 | 50 | 450 | 1.600 | D |
| G | 240.0 | Cellulose fibre [040; 50] | 0.040 | 1 | 50 | 2.000 | Е |
| Н | 15.0 | OSB (sealed with airtight tape) | 0.130 | 200 | 600 | 1.700 | D |
| I | 12.5 | gypsum plaster board type DF or | 0.250 | 10 | 800 | 1.050 | A2 |
| 1 | 12.5 | gypsum fibre board | 0.320 | 21 | 1000 | 1.100 | A2 |

Sustainability rating (per m²)

Database ecoinvent

OI3_{Kon} 22.3

Calculated by HFA



Designation: awrhho07a-14 Last updated:

8/2/23 Holzforschung Austria Source:

HFA, SP Editor:

Details of sustainability rating

Database ecoinvent

| Lifecycle | GWP | AP | EP | ODP | POCP | |
|-----------------------|--------------------------|--------------------------|--------------------------|---------------|---------------|---------------|
| (Phases) | [kg CO ₂ -e.] | [kg SO ₂ -e.] | [kg PO ₄ -e.] | [kg R11-e.] | [kg Ethen-e.] | |
| A1 - A3 | | 0.129 | 0.057 | 2,18E-6 | 0.025 | |
| | | | | | | |
| | | | | | | |
| Lifecycle | PERE | PERM | PERT | PENRE | PENRM | PENRT |
| Lifecycle (Phases) | PERE [MJ] | PERM [MJ] | PERT [MJ] | PENRE [MJ] | PENRM [MJ] | PENRT [MJ] |