

Designation: awrohi01b-00 Last updated: 8/2/23

Source: Holzforschung Austria

Editor: HFA, SP

External wall - awrohi01b-00

external wall, timber frame construction, not ventilated, with dry lining, with cladding, other surface


Performance rating

Thermal performance	U Diffusion	0.18 W/(m ² K) suitable		
Calculated by HFA				
Acoustic performance	R _w (C;C _{tr}) L _{n,w} (C _I)	54(-2;-8) dB		

battens for the dry lining mounted offset without using resilient clips will result in Rw(C;Ctr)=51(-2;-6) dB Assessed by MA39

 $\label{eq:mass_per_unit_area} \mbox{Mass per unit area} \qquad \mbox{m} \qquad \qquad 76.50 \mbox{ kg/m}^2$

Calculation based on GF

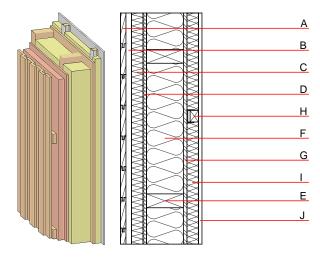

Note: e=625

Register of building materials used for this application, cross-section (from outside to inside, dimensions in mm)

	Thickness	Building material	Thermal performance				Reaction to fire	
			λ	μ min – max	ρ	С	EN	
Α	24.0	larch wood external wall cladding	0.155	150	600	1.600	D	
В	24.0	spruce wood cross battens	0.120	50	450	1.600	D	
С	50.0	wood wool composite boards	0.090	2 - 5	370	2.000	В	
D	15.0	fibreboard (MDF)	0.140	11	600	1.700	D	
E	160.0	construction timber (60/; e=*)	0.120	50	450	1.600	D	
F	160.0	mineral wool [040; ≥16; <1000°C]	0.040	1	16	1.030	A1	
G	15.0	OSB (sealed with airtight tape)	0.130	200	600	1.700	D	
Н	40.0	spruce wood battens offset mounted on resilient clips	0.120	50	450	1.600	D	
I	40.0	mineral wool [040; ≥16; <1000°C] or air layer in type 02	0.040	1	16	1.030	A1	
J	15.0	gypsum fibre board or	0.320	21	1000	1.100	A2	
J	15.0	gypsum plaster board type DF	0.250	10	800	1.050	A2	

$\textbf{Sustainability rating} \ (\text{per } \text{m}^2)$

Database ecoinvent

OI3_{Kon} 28.3

Calculated by HFA



Designation: awrohi01b-00 8/2/23 Holzforschung Austria Last updated:

Source:

HFA, SP Editor:

Details of sustainability rating

Database ecoinvent

Lifecycle	GWP	AP	EP	ODP	POCP	
(Phases)	[kg CO ₂ -e.]	[kg SO ₂ -e.]	[kg PO ₄ -e.]	[kg R11-e.]	[kg Ethen-e.]	
A1 - A3		0.140	0.060	2,53E-6	0.027	
Lifecycle	PERE	PERM	PERT	PENRE	PENRM	PENRT
(Phases)	[MJ]	[MJ]	[MJ]	[MJ]	[MJ]	[MJ]
A1 - A3	130.910	789.275	920.185	486.334	28.891	515.226