

Designation: awrohi02a-04 Last updated: 8/2/23

Holzforschung Austria Source:

Editor: HFA, SP

## External wall - awrohi02a-04

external wall, timber frame construction, not ventilated, with dry lining, with cladding, other surface

### Performance rating


Fire protection **REI** from inside 60 performance REI from outside 30 maximum ceiling height = 3 m; maximum load  $E_{d,fi}$  = 19,2 kN/m Classified by HFA

Thermal performance	U Diffusion	0.13 W/(m <sup>2</sup> K) suitable
Calculated by HFA		
Acoustic performance	$R_w$ (C;C <sub>tr</sub> ) $L_{n,w}$ (C <sub>I</sub> )	52(-3;-9) dB
Vartical battons for the di	a lining scrowed onto	the ledger beams lead to an

Assessed by MA39

Mass per unit area  $69.50 \text{ kg/m}^2$ 

Calculation based on GF

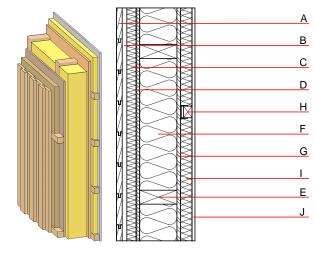

Note: e=625

## Register of building materials used for this application, cross-section (from outside to inside, dimensions in mm)

	Thickness	Building material	Thermal performance				Reaction to fire
			λ	μ min – max	ρ	С	EN
Α	24.0	larch wood external wall cladding	0.155	150	600	1.600	D
В	50.0	spruce wood cross battens	0.120	50	450	1.600	D
С	40.0	softboard [045; 250] - rigid underlay	0.045	5	250	2.100	Е
D	15.0	fibreboard (MDF)	0.140	11	600	1.700	D
Е	240.0	construction timber (60/; e=*)	0.120	50	450	1.600	D
F	240.0	mineral wool [040; ≥16; <1000°C]	0.040	1	16	1.030	A1
G	15.0	OSB (sealed with airtight tape)	0.130	200	600	1.700	D
Н	40.0	spruce wood cross battens (a=400) or battens offset)	0.120	50	450	1.600	D
I	40.0	mineral wool [040; ≥16; <1000°C] or air layer in type 02	0.040	1	16	1.030	A1
J	12.5	gypsum fibre board or	0.320	21	1000	1.100	A2
J	12.5	gypsum plaster board type DF	0.250	10	800	1.050	A2

# Sustainability rating (per m<sup>2</sup>)

Database ecoinvent

35.7 OI3<sub>Kon</sub>

Calculated by HFA



Designation: awrohi02a-04 Last updated:

8/2/23 Holzforschung Austria Source:

HFA, SP Editor:

## Details of sustainability rating

### Database ecoinvent

Lifecycle	GWP	AP	EP	ODP	POCP	
(Phases)	[kg CO <sub>2</sub> -e.]	[kg SO <sub>2</sub> -e.]	[kg PO <sub>4</sub> -e.]	[kg R11-e.]	[kg Ethen-e.]	
A1 - A3		0.178	0.079	3,05E-6	0.033	
Lifecycle	PERE	PERM	PERT	PENRE	PENRM	PENRT
(Phases)	[MJ]	[MJ]	[MJ]	[MJ]	[MJ]	[MJ]
A1 - A3	155.978	936.250	1092.228	595.455	42.896	638.351