

Designation: awrohi02a-06 Last updated: 8/2/23

Holzforschung Austria Source:

Editor: HFA, SP

# External wall - awrohi02a-06

external wall, timber frame construction, not ventilated, with dry lining, with cladding, other surface

### Performance rating


Fire protection **REI** from inside 60 performance REI from outside 30 maximum ceiling height = 3 m; maximum load  $E_{d,fi}$  = 19,2 kN/m Classified by HFA

Thermal performance	U Diffusion	0.12 W/(m <sup>2</sup> K) suitable
Calculated by HFA		
Acoustic performance	R <sub>w</sub> (C;C <sub>tr</sub> ) L <sub>n,w</sub> (C <sub>I</sub> )	52(-3;-9) dB
Vertical battens for the dr Rw(C:Ctr)=49(-1:-5) dB	y lining screwed onto	the ledger beams lead to an

Assessed by MA39

Mass per unit area  $72.60 \text{ kg/m}^2$ 

Calculation based on GF

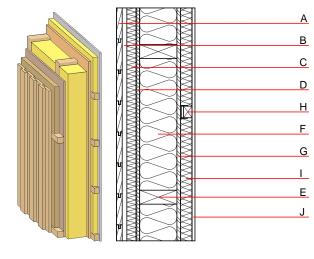

Note: e=625

## Register of building materials used for this application, cross-section (from outside to inside, dimensions in mm)

	Thickness	Building material	Thermal performance				Reaction to fire
			λ	μ min – max	ρ	С	EN
Α	24.0	larch wood external wall cladding	0.155	150	600	1.600	D
В	50.0	spruce wood cross battens	0.120	50	450	1.600	D
С	40.0	softboard [045; 250] - rigid underlay	0.045	5	250	2.100	E
D	15.0	fibreboard (MDF)	0.140	11	600	1.700	D
Е	240.0	construction timber (60/; e=*)	0.120	50	450	1.600	D
F	240.0	mineral wool [040; ≥16; <1000°C]	0.040	1	16	1.030	A1
G	15.0	OSB (sealed with airtight tape)	0.130	200	600	1.700	D
Н	80.0	spruce wood cross battens (a=400) or battens offset)	0.120	50	450	1.600	D
I	80.0	mineral wool [040; ≥16; <1000°C] or air layer in type 02	0.040	1	16	1.030	A1
J	12.5	gypsum fibre board or	0.320	21	1000	1.100	A2
J	12.5	gypsum plaster board type DF	0.250	10	800	1.050	A2

## Sustainability rating (per m<sup>2</sup>)

Calculated by HFA

Database ecoinvent 38.0 OI3<sub>Kon</sub>

dataholz.eu - Catalogue of timber building materials, components and component connections reviewed to consider thermal, acoustic, fire performance requirements and ecological drivers for timber construction released by accredited testing institutes.



Designation: awrohi02a-06 Last updated:

8/2/23 Holzforschung Austria Source:

HFA, SP Editor:

## Details of sustainability rating

#### Database ecoinvent

Lifecycle	GWP	AP	EP	ODP	POCP	
(Phases)	[kg CO <sub>2</sub> -e.]	[kg SO <sub>2</sub> -e.]	[kg PO <sub>4</sub> -e.]	[kg R11-e.]	[kg Ethen-e.]	
A1 - A3		0.190	0.085	3,25E-6	0.035	
Lifecycle	PERE	PERM	PERT	PENRE	PENRM	PENRT
(Phases)	[MJ]	[MJ]	[MJ]	[MJ]	[MJ]	[MJ]
A1 - A3	164.665	985.384	1150.048	630.613	42.896	673.510