dataholz.eu


Designation: Last updated: Source: Editor: awrohi03a-11 8/2/23 Holzforschung Austria HFA, SP

External wall - awrohi03a-11

external wall, timber frame construction, not ventilated, with dry lining, with cladding, other surface

Performance rating

Fire protection performance maximum ceiling height = Classified by HFA	REI from inside REI from outside 3 m; maximum load E _{d,fi} =	60 30 32,0 kN/m
Thermal performance Calculated by HFA	U Diffusion	0.19 W/(m ² K) suitable
Acoustic performance	R _w (C;C _{tr}) L _{n,w} (C _l)	50(-3;-9) dB
Vertical external battens a ledger beams lead to an R Assessed by MA39	nd vertical battens for the c w(C;Ctr)=43(-1;-5) dB	try lining screwed onto the
Mass per unit area	m	74.30 kg/m ²

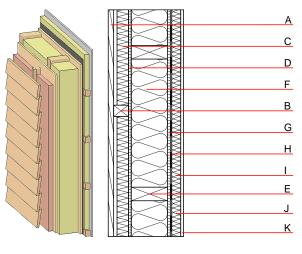

Calculation based on GF

Note: e=400

Register of building materials used for this application, cross-section (from outside to inside, dimensions in mm)

	Thickness	Building material	Thermal per	formance			Reaction to fire
			λ	µ min – max	ρ	с	EN
4	24.0	larch wood external wall cladding	0.155	150	600	1.600	D
3	65.0	spruce wood cross battens of battens offset	0.120	50	450	1.600	D
2	50.0	wood wool composite boards	0.090	2 - 5	370	2.000	В
D	16.0	particleboard	0.130	50 - 100	700	1.700	D
-	160.0	construction timber (60/; $e=*$)	0.120	50	450	1.600	D
-	160.0	mineral wool [040; ≥16; <1000°C]	0.040	1	16	1.030	A1
5	12.0	particleboard	0.130	50 - 100	700	1.700	D
Η		vapour barrier sd≥ 10m			1000		
	40.0	spruce wood cross battens (a=400) or battens offset)	0.120	50	450	1.600	D
	40.0	mineral wool [040; ≥16; <1000°C]	0.040	1	16	1.030	A1
<	12.5	gypsum fibre board or	0.320	21	1000	1.100	A2
<	12.5	gypsum plaster board type DF	0.250	10	800	1.050	A2

Sustainability rating (per m²)

Database ecoinvent

OI3_{Kon}

Calculated by HFA

27.3

dataholz.eu

Designation: Last updated: Source: Editor: awrohi03a-11 8/2/23 Holzforschung Austria HFA, SP

Details of sustainability rating

Database ecoinvent

Lifecycle	GWP	AP	EP	ODP	POCP	
(Phases)	[kg CO ₂ -e.]	[kg SO ₂ -e.]	[kg PO ₄ -e.]	[kg R11-e.]	[kg Ethen-e.]	
A1 - A3		0.133	0.057	2,42E-6	0.032	
Lifecycle	PERE	PERM	PERT	PENRE	PENRM	PENRT
(Phases)	[LM]	[M]	[LM]	[LM]	[M]	[LM]
A1 - A3	114.418	849.484	963.902	508.084	41.362	549.447