

Designation: awroho01b-04 Last updated: 8/2/23

Source: Holzforschung Austria

Editor: HFA, SP


External wall - awroho01b-04

external wall, timber frame construction, not ventilated, without dry lining, with cladding, other surface

Performance rating

-		
Thermal performance	U Diffusion	0.19 W/(m ² K) suitable
Calculated by HFA		
Acoustic performance	R _w (C;C _{tr}) L _{n,w} (C _l)	52(-1;-6) dB
Assessed by MA39		
Mass per unit area	m	80.70 kg/m²

Calculation based on GF

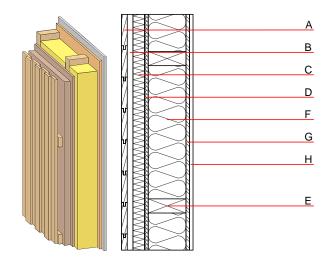

Note: e=625

Register of building materials used for this application, cross-section (from outside to inside, dimensions in mm)

	Thickness	Building material	Thermal pe	rformance			Reaction to fire
			λ	μ min – max	ρ	С	EN
Α	24.0	larch wood external wall cladding	0.155	150	600	1.600	D
В	24.0	spruce wood cross battens	0.120	50	450	1.600	D
С	50.0	wood wool composite boards	0.090	2 - 5	370	2.000	В
D	15.0	fibreboard (MDF)	0.140	11	600	1.700	D
E	160.0	construction timber (60/; e=*)	0.120	50	450	1.600	D
F	160.0	mineral wool [035; 50; <1000°C]	0.035	1	50	1.030	A1
G	15.0	OSB (sealed with airtight tape)	0.130	200	600	1.700	D
Н	15.0	gypsum fibre board or	0.320	21	1000	1.100	A2
Н	15.0	gypsum plaster board type DF	0.250	10	800	1.050	A2

Sustainability rating (per m²)

Database ecoinvent

Ol3_{Kon} 43.8

Calculated by HFA



Designation: awroho01b-04 8/2/23 Holzforschung Austria Last updated:

Source:

HFA, SP Editor:

Details of sustainability rating

Database ecoinvent

Lifecycle	GWP	AP	EP	ODP	POCP	
(Phases)	[kg CO ₂ -e.]	[kg SO ₂ -e.]	[kg PO ₄ -e.]	[kg R11-e.]	[kg Ethen-e.]	
A1 - A3		0.197	0.086	3,54E-6	0.032	
Lifecycle	PERE	PERM	PERT	PENRE	PENRM	PENRT
(Phases)	[MJ]	[MI]	[MJ]	[MJ]	[MJ]	[MJ]
A1 - A3	133.687	752.424	886.111	661.403	28.891	690.294