

Designation: awropi03a-13 8/2/23 Last updated:

Holzforschung Austria Source:

Editor: HFA, SP

External wall - awropi03a-13

external wall, timber frame construction, not ventilated, with dry lining, with rendering, other surface

Performance rating


REI from inside 60 Fire protection performance RFI from outside 30 maximum ceiling height = 3 m; maximum load $E_{d,fi}$ = 19,2 kN/m Classified by HFA

Thermal performance Calculated by HFA	U Diffusion	0.17 W/(m ² K) suitable
Acoustic performance	R _w (C;C _{tr}) L _{n.w} (C _l)	48(-3;-6) dB

EPS-F with a dynamic stiffness of $s' = 20MN/m^3$. Vertical battens for the dry lining screwed onto the structural timber lead to an Rw(C;Ctr)=42(-1;-5) dB Assessed by MA39

Mass per unit area 50.80 kg/m^2

Calculation based on gypsum plaster board type DF

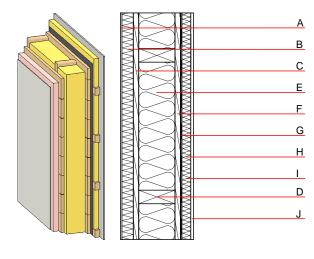

Note: e=625

Register of building materials used for this application, cross-section (from outside to inside, dimensions in mm)

	Thickness	Building material	Thermal performance				Reaction to fire	
			λ	μ min – max	ρ	С	EN	
Α	4.0	plaster	1.000	10 - 35	2000	1.130	A1	
В	50.0	Polystyrene EPS-F [0,040]	0.040	20 - 50	17	1.450	Е	
С	25.0	planking spruce wood	0.120	50	450	1.600	D	
D	160.0	construction timber (60/; e=*)	0.120	50	450	1.600	D	
Е	160.0	mineral wool [040; ≥16; <1000°C]	0.040	1	16	1.030	A1	
F	25.0	planking spruce wood	0.120	50	450	1.600	D	
G		vapour barrier sd≥ 16m			1000			
Н	40.0	spruce wood cross battens (a=400) or battens offset)	0.120	50	450	1.600	D	
I	40.0	mineral wool [040; ≥16; <1000°C] or air layer in type 02	0.040	1	16	1.030	A1	
J	12.5	gypsum plaster board type DF or	0.250	10	800	1.050	A2	
J	12.5	gypsum fibre board	0.320	21	1000	1.100	A2	

Sustainability rating (per m²)

Database ecoinvent OI3_{Kon} 23.0 Calculated by HFA



Designation: awropi03a-13 8/2/23 Holzforschung Austria Last updated:

Source:

HFA, SP Editor:

Details of sustainability rating

Database ecoinvent

Lifecycle	GWP	AP	EP	ODP	POCP	
(Phases)	[kg CO ₂ -e.]	[kg SO ₂ -e.]	[kg PO ₄ -e.]	[kg R11-e.]	[kg Ethen-e.]	
A1 - A3		0.113	0.047	2,01E-6	0.029	
Lifecycle	PERE	PERM	PERT	PENRE	PENRM	PENRT
(Phases)	[MJ]	[MJ]	[MJ]	[MJ]	[MJ]	[MJ]
A1 - A3	102.109	576.178	678.287	370.382	36.048	406.430