

Designation: awropi07a-03 Last updated: 8/2/23

Holzforschung Austria Source:

Editor: HFA, SP

External wall - awropi07a-03

external wall, timber frame construction, not ventilated, with dry lining, with rendering, other surface


Performance rating

REI from inside 60 Fire protection performance RFI from outside 30 maximum ceiling height = 3 m; maximum load $E_{d,fi}$ = 32,0 kN/m Classified by HFA

Thermal performance	U Diffusion	$0.15 \text{ W/(m}^2\text{K)}$ suitable
Calculated by HFA		
Acoustic performance	R _w (C;C _{tr}) L _{n,w} (C _l)	46(-3;-6) dB
vertical battens for the dr	y lining screwed onto	the structural timber lead to an

Rw(C;Ctr)=43(-1;-5) dB Assessed by MA39

Mass per unit area Calculation based on gypsum plaster board type DF 52.20 kg/m^2

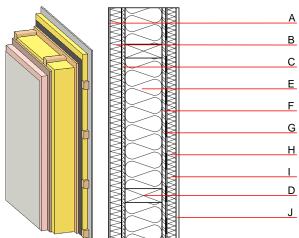

Note: e=625

Register of building materials used for this application, cross-section (from outside to inside, dimensions in mm)

	Thickness	Building material	Thermal per	rformance			Reaction to fire
			λ	μ min – max	ρ	С	EN
Α	4.0	plaster	1.000	10 - 35	2000	1.130	A1
В	50.0	Polystyrene EPS-F [0,040]	0.040	20 - 50	17	1.450	E
С	15.0	fibreboard (MDF)	0.140	11	600	1.700	D
D	200.0	construction timber (60/; e=*)	0.120	50	450	1.600	D
E	200.0	mineral wool [040; ≥16; <1000°C]	0.040	1	16	1.030	A1
F	15.0	OSB	0.130	200	600	1.700	D
G		vapour barrier sd≥ 9m			1000		
Н	40.0	spruce wood cross battens (a=400) or battens offset)	0.120	50	450	1.600	D
I	40.0	mineral wool [040; ≥16; <1000°C] or air layer in type 02	0.040	1	16	1.030	A1
J	12.5	gypsum plaster board type DF or	0.250	10	800	1.050	A2
J	12.5	gypsum fibre board	0.320	21	1000	1.100	A2

Sustainability rating (per m²)

Database ecoinvent OI3_{Kon}

Calculated by HFA

34.1



Designation: awropi07a-03 8/2/23 Holzforschung Austria Last updated:

Source:

Editor: HFA, SP

Details of sustainability rating

Database ecoinvent

Lifecycle	GWP	AP	EP	ODP	POCP	
(Phases)	[kg CO ₂ -e.]	[kg SO ₂ -e.]	[kg PO ₄ -e.]	[kg R11-e.]	[kg Ethen-e.]	
A1 - A3		0.142	0.059	2,38E-6	0.027	
Lifecycle	PERE	PERM	PERT	PENRE	PENRM	PENRT
	FA 4 13	FAA13	[MJ]	[MJ]	[MJ]	[MJ]
(Phases)	[MJ]	[MJ]	[INI]	LIAIT	[IAI2]	[LIA12]