

Designation: awropi11a-07 Last updated: 8/2/23

Holzforschung Austria Source:

Editor: HFA, SP

# External wall - awropi11 a-07

external wall, timber frame construction, not ventilated, with dry lining, with rendering, other surface

### Performance rating


**REI** from inside 60 Fire protection performance REI from outside 60 maximum ceiling height = 3 m; maximum load  $E_{d,fi}$  = 32,0 kN/m Classified by HFA

Thermal performance	U Diffusion	$0.17 \text{ W/(m}^2\text{K)}$ suitable
Calculated by HFA		
Acoustic performance	R <sub>w</sub> (C;C <sub>tr</sub> ) L <sub>n,w</sub> (C <sub>l</sub> )	53(-3;-8) dB

Rw(C;Ctr)=50(-1;-5) dB Assessed by MA39

Mass per unit area  $71.70 \text{ kg/m}^2$ 

Calculation based on gypsum plaster board type DF

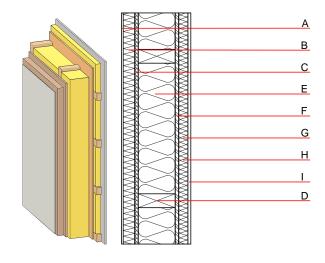

Note: e=625

### Register of building materials used for this application, cross-section (from outside to inside, dimensions in mm)

	Thickness	Building material	Thermal performance				Reaction to fire
			λ	μ min – max	ρ	С	EN
Α	10.0	plaster	1.000	10 - 35	2000	1.130	A1
В	50.0	wood wool composite boards	0.090	2 - 5	370	2.000	В
С	15.0	fibreboard (MDF)	0.140	11	600	1.700	D
D	160.0	construction timber (60/; e=*)	0.120	50	450	1.600	D
Ε	160.0	mineral wool [035; 50; <1000°C]	0.035	1	50	1.030	A1
F	15.0	OSB (sealed with airtight tape)	0.130	200	600	1.700	D
G	40.0	spruce wood cross battens (a=400) or battens offset)	0.120	50	450	1.600	D
Н	40.0	mineral wool [035; 50; <1000°C] or air layer in type 02	0.035	1	50	1.030	A1
T	12.5	gypsum plaster board type DF or	0.250	10	800	1.050	A2
T	12.5	gypsum fibre board	0.320	21	1000	1.100	A2

## Sustainability rating (per m<sup>2</sup>)

Database ecoinvent						
OI3 <sub>Kon</sub>	53.0					
Calculated by HFA						



Designation: awropi11a-07 8/2/23 Holzforschung Austria Last updated:

Source:

Editor: HFA, SP

## Details of sustainability rating

#### Database ecoinvent

Lifecycle	GWP	AP	EP	ODP	POCP	
(Phases)	[kg CO <sub>2</sub> -e.]	[kg SO <sub>2</sub> -e.]	[kg PO <sub>4</sub> -e.]	[kg R11-e.]	[kg Ethen-e.]	
A1 - A3		0.220	0.096	4,02E-6	0.030	
Lifecycle	PERE	PERM	PERT	PENRE	PENRM	PENRT
(Phases)	[MJ]	[MJ]	[MJ]	[MJ]	[MJ]	[MJ]
A1 - A3	103.974	560.422	664.396	733.108	29.196	762.305