dataholz.eu


Designation: Last updated: Source: Editor: awropi15b-00 8/2/23 Holzforschung Austria HFA, SP

External wall - awropi15b-00

external wall, timber frame construction, not ventilated, with dry lining, with rendering, other surface

Performance rating

Fire protection performance maximum ceiling height = Classified by HFA	REI from inside REI from outside 3 m; maximum load $E_{d,fi} = 3$	60 60 82,0 kN∕m
Thermal performance Calculated by HFA	U Diffusion	0.17 W∕(m ² K) suitable
Acoustic performance	R _w (C;C _{tr}) L _{n,w} (C _l)	52(-2;-9) dB
Vertical battens for the dry Rw(C;Ctr)=50(-1;-7) dB Assessed by MA39	lining screwed onto the led	ger beams lead to an
Mass per unit area	m	76.20 kg/m ²

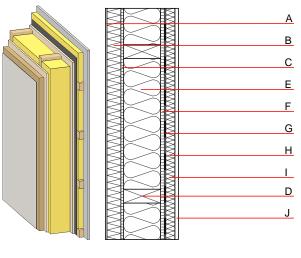

Calculation based on gypsum plaster board type DF

Note: e=625

Register of building materials used for this application, cross-section (from outside to inside, dimensions in mm)

	Thickness	Building material	Thermal per	formance			Reaction to fire
			λ	µ min – max	ρ	с	EN
4	7.0	plaster	1.000	10 - 35	2000	1.130	A1
3	60.0	wood-fibre insulation board WF-PT [045; 180]	0.045	5 - 7	180	2.100	E
2	12.0	particleboard P5	0.130	50 - 100	700	1.700	D
D	160.0	construction timber (60/; $e=*$)	0.120	50	450	1.600	D
1	160.0	mineral wool [040; ≥16; <1000°C]	0.040	1	16	1.030	A1
-	16.0	particleboard P4	0.130	50 - 100	700	1.700	D
Ĵ		vapour barrier sd≥ 7m			1000		
H	40.0	spruce wood cross battens (a=400) or battens offset)	0.120	50	450	1.600	D
	40.0	mineral wool [040; ≥16; <1000°C]	0.040	1	16	1.030	A1
	15.0	gypsum plaster board type DF or	0.250	10	800	1.050	A2
	15.0	gypsum fibre board	0.320	21	1000	1.100	A2

Sustainability rating (per m²)

Database ecoinvent

OI3_{Kon}

Calculated by HFA

43.7

dataholz.eu

Designation: Last updated: Source: Editor: awropi15b-00 8/2/23 Holzforschung Austria HFA, SP

Details of sustainability rating

Database ecoinvent

Lifecycle	GWP	AP	EP	ODP	POCP	
(Phases)	[kg CO ₂ -e.]	[kg SO ₂ -e.]	[kg PO ₄ -e.]	[kg R11-e.]	[kg Ethen-e.]	
A1 - A3		0.176	0.078	3,33E-6	0.030	
Lifecycle	PERE	PERM	PERT	PENRE	PENRM	PENRT
(Phases)	[LM]	[LM]	[MJ]	[LM]	[MJ]	[MJ]
A1 - A3	78.218	698.627	776.845	684.123	73.105	757.228

dataholz.eu – Catalogue of timber building materials, components and component connections reviewed to consider thermal, acoustic, fire performance requirements and ecological drivers for timber construction released by accredited testing institutes. These datasheets will generally be accepted as proofs of compliance by building authorities.