

Designation: awropi16b-11 Last updated: 8/2/23

Source: Holzforschung Austria

Editor: HFA, SP

External wall - awropi16b-11

external wall, timber frame construction, not ventilated, with dry lining, with rendering, other surface


Performance rating

U Diffusion	0.18 W/(m ² K) suitable	
R _w (C;C _{tr}) L _{n,w} (C _I)	52(-2;-9) dB	
	Diffusion R _w (C;C _{tr})	Diffusion suitable R _w (C;C _{tr}) 52(-2;-9) dB

Vertical battens for the dry lining screwed onto the ledger beams lead to an Rw(C;Ctr)=50(-1;-7) dB Assessed by MA39

 $\begin{tabular}{lll} \begin{tabular}{lll} \begin{$

Calculation based on gypsum plaster board type DF

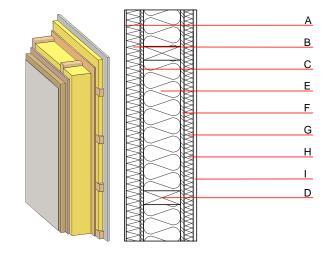

Note: e=400

Register of building materials used for this application, cross-section (from outside to inside, dimensions in mm)

	Thickness	Building material	Thermal pe	rformance			Reaction to fire
			λ	μ min – max	ρ	С	EN
Α	7.0	plaster	1.000	10 - 35	2000	1.130	A1
В	60.0	wood-fibre insulation board WF-PT [045; 180]	0.045	5 - 7	180	2.100	Е
С	15.0	fibreboard (MDF)	0.140	11	600	1.700	D
D	160.0	construction timber (60/; e=*)	0.120	50	450	1.600	D
E	160.0	mineral wool [040; ≥16; <1000°C]	0.040	1	16	1.030	A1
F	15.0	OSB (sealed with airtight tape)	0.130	200	600	1.700	D
G	40.0	spruce wood cross battens (a=400) or battens offset)	0.120	50	450	1.600	D
Н	40.0	mineral wool [040; ≥16; <1000°C]	0.040	1	16	1.030	A1
I	15.0	gypsum plaster board type DF or	0.250	10	800	1.050	A2
1	15.0	gypsum fibre board	0.320	21	1000	1.100	A2

Sustainability rating (per m²)

Database ecoinvent

OI3_{Kon} 41.8

Calculated by HFA



Designation: awropi16b-11 8/2/23 Holzforschung Austria Last updated:

Source:

Editor: HFA, SP

Details of sustainability rating

Database ecoinvent

	1	1	1	1	1	1
Lifecycle	GWP	AP	EP	ODP	POCP	
(Phases)	[kg CO ₂ -e.]	[kg SO ₂ -e.]	[kg PO ₄ -e.]	[kg R11-e.]	[kg Ethen-e.]	
A1 - A3		0.183	0.081	3,38E-6	0.028	
Lifecycle	PERE	PERM	PERT	PENRE	PENRM	PENRT
(Phases)	[MJ]	[MJ]	[MJ]	[MJ]	[MJ]	[MJ]
A1 - A3	123.928	777.137	901.065	645.033	58.943	703.976