

Designation: awropi16b-08 Last updated: 8/2/23

Holzforschung Austria Source:

Editor: HFA, SP

# External wall - awropi16b-08

external wall, timber frame construction, not ventilated, with dry lining, with rendering, other surface

### Performance rating


**REI** from inside 60 Fire protection performance RFI from outside 90 maximum ceiling height = 3 m; maximum load  $E_{d,fi}$  = 32,0 kN/m Classified by HFA

	Diffusion	suitable	
alculated by HFA			
coustic performance	R <sub>w</sub> (C;C <sub>tr</sub> ) L <sub>n,w</sub> (C <sub>l</sub> )	52(-2;-9) dB	
•	L <sub>n,w</sub> (C <sub>l</sub> )	52(-2;-9) dB the ledger beams lead to a	_

Rw(C;Ctr)=50(-1;-7) dB Assessed by MA39

Mass per unit area  $78.30 \text{ kg/m}^2$ 

Calculation based on gypsum plaster board type DF

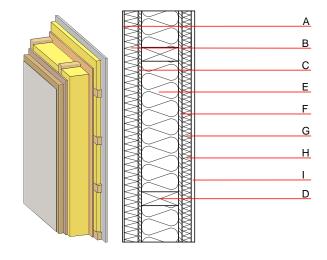

Note: e=625

### Register of building materials used for this application, cross-section (from outside to inside, dimensions in mm)

	Thickness	Building material		hermal performance Reaction to fire			Reaction to fire
			λ	μ min – max	ρ	С	EN
Α	7.0	plaster	1.000	10 - 35	2000	1.130	A1
В	60.0	wood-fibre insulation board WF-PT [045; 180]	0.045	5 - 7	180	2.100	E
С	15.0	fibreboard (MDF)	0.140	11	600	1.700	D
D	160.0	construction timber (60/; e=*)	0.120	50	450	1.600	D
Ε	160.0	mineral wool [038; ≥33; ≥1000°C]	0.038	1	33	1.030	A1
F	15.0	OSB (sealed with airtight tape)	0.130	200	600	1.700	D
G	40.0	spruce wood cross battens (a=400) or battens offset)	0.120	50	450	1.600	D
Н	40.0	mineral wool [038; ≥33; ≥1000°C]	0.038	1	33	1.030	A1
I	15.0	gypsum plaster board type DF or	0.250	10	800	1.050	A2
1	15.0	gypsum fibre board	0.320	21	1000	1.100	A2

## Sustainability rating (per m<sup>2</sup>)

Database ecoinvent	
OI3 <sub>Kon</sub>	48.0
Calculated by HFA	



Designation: awropi16b-08 Last updated:

8/2/23 Holzforschung Austria Source:

HFA, SP Editor:

## Details of sustainability rating

#### Database ecoinvent

Lifecycle	GWP	AP	EP	ODP	POCP	
(Phases)	[kg CO <sub>2</sub> -e.]	[kg SO <sub>2</sub> -e.]	[kg PO <sub>4</sub> -e.]	[kg R11-e.]	[kg Ethen-e.]	
A1 - A3		0.217	0.080	3,01E-6	0.057	
Lifecycle	PERE	PERM	PERT	PENRE	PENRM	PENRT
(Phases)	[MJ]	[MJ]	[MJ]	[MJ]	[MJ]	[MJ]
A1 - A3	110.428	706.384	816.812	642.908	58.943	701.851