

Designation: awropi20a-06 Last updated: 8/2/23

Source: Holzforschung Austria

Editor: HFA, SP

# External wall - awropi20a-06

external wall, timber frame construction, not ventilated, with dry lining, with rendering, other surface

## Performance rating


Fire protection performance REI from inside 60 performance REI from outside 60 maximum ceiling height = 3 m; maximum load  $E_{d,fi} = 32,0 \text{ kN/m}$ 

U Diffusion	0.12 W/(m <sup>2</sup> K) suitable
R <sub>w</sub> (C;C <sub>tr</sub> ) L <sub>n,w</sub> (C <sub>l</sub> )	54(-3;-11) dB
	R <sub>w</sub> (C;C <sub>tr</sub> )

Rw(C;Ctr)=52(-2;-8) dB Assessed by MA39

Mass per unit area m

Calculation based on gypsum plaster board type DF

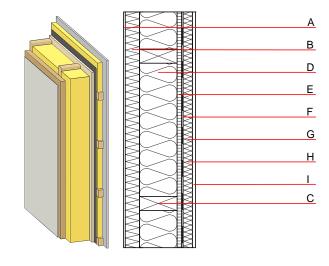

Note: e=625

### Register of building materials used for this application, cross-section (from outside to inside, dimensions in mm)

 $73.70 \text{ kg/m}^2$ 

	Thickness	Building material	Thermal performance				Reaction to fire	
			λ	μ min – max	ρ	С	EN	
Α	7.0	plaster	1.000	10 - 35	2000	1.130	A1	
В	60.0	wood-fibre insulation board WF-PT [045; 180]	0.045	5 - 7	180	2.100	Е	
С	240.0	construction timber (60/; e=*)	0.120	50	450	1.600	D	
D	240.0	mineral wool [040; ≥16; <1000°C]	0.040	1	16	1.030	A1	
Е	19.0	particleboard	0.130	50 - 100	700	1.700	D	
F		vapour barrier sd≥ 2m			1000			
G	80.0	spruce wood cross battens (a=400) or battens offset)	0.120	50	450	1.600	D	
Н	80.0	mineral wool [040; ≥16; <1000°C] or air layer in type 02	0.040	1	16	1.030	A1	
1	12.5	gypsum plaster board type DF or	0.250	10	800	1.050	A2	
I	12.5	gypsum fibre board	0.320	21	1000	1.100	A2	

#### Sustainability rating (per m<sup>2</sup>)

Database ecoinvent

Ol3<sub>Kon</sub> 47.8

Calculated by HFA



Designation: awropi20a-06 Last updated:

8/2/23 Holzforschung Austria Source:

HFA, SP Editor:

## Details of sustainability rating

#### Database ecoinvent

Lifecycle	GWP	AP	EP	ODP	POCP	
(Phases)	[kg CO <sub>2</sub> -e.]	[kg SO <sub>2</sub> -e.]	[kg PO <sub>4</sub> -e.]	[kg R11-e.]	[kg Ethen-e.]	
A1 - A3		0.198	0.089	3,72E-6	0.033	
Lifecycle	PERE	PERM	PERT	PENRE	PENRM	PENRT
(Phases)	[MJ]	[MJ]	[MJ]	[MJ]	[MJ]	[MJ]
A1 - A3	96.185	710.569	806.754	722.532	57.446	779.978