

Designation: awropi24a-07 Last updated: 8/2/23

Source: Holzforschung Austria


Editor: HFA, PLB

# External wall - awropi24a-07

external wall, timber frame construction, not ventilated, with dry lining, with rendering, wooden surface

### Performance rating

Thermal performance	U Diffusion	0.13 W/(m <sup>2</sup> K) suitable
Calculated by HFA		
Acoustic performance	R <sub>w</sub> (C;C <sub>tr</sub> ) L <sub>n,w</sub> (C <sub>I</sub> )	50(-3;-10) dB
Assessed by TGM		
Mass per unit area	m	70.40 kg/m <sup>2</sup>

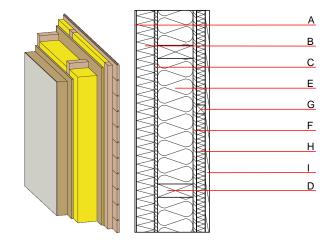

# Register of building materials used for this application, cross-section (from outside to inside, dimensions in mm)

	Thickness	Building material	Thermal pe	rformance			Reaction to fire
			λ	μ min – max	ρ	С	EN
Α	7.0	plaster	1.000	10 - 35	2000	1.130	A1
В	80.0	WF-PT [042; 180]	0.042	3 - 7	180	2.100	E
С	15.0	fibreboard (MDF)	0.140	11	600	1.700	D
D	160.0	construction timber (60/; e=625)	0.120	50	450	1.600	D
Ε	160.0	mineral wool [038; ≥33; ≥1000°C]	0.038	1	33	1.030	A1
F	15.0	OSB (sealed with airtight tape)	0.130	200	600	1.700	D
G	40.0	spruce wood cross battens (a=400) or battens offset)	0.120	50	450	1.600	D
Н	40.0	mineral wool [038; ≥33; ≥1000°C]	0.038	1	33	1.030	A1
1	19.0	planking tongue and groove	0.120	50	450	1.600	D

## Sustainability rating (per m<sup>2</sup>)

Database ecoinvent

013<sub>Kon</sub> 44.4

Calculated by HFA



Designation: awropi24a-07 8/2/23 Holzforschung Austria Last updated:

Source:

HFA, PLB Editor:

# Details of sustainability rating

### Database ecoinvent

Lifecycle	GWP	AP	EP	ODP	POCP	
(Phases)	[kg CO <sub>2</sub> -e.]	[kg SO <sub>2</sub> -e.]	[kg PO <sub>4</sub> -e.]	[kg R11-e.]	[kg Ethen-e.]	
A1 - A3		0.218	0.081	2,79E-6	0.060	
Lifecycle	PERE	PERM	PERT	PENRE	PENRM	PENRT
		1		F3.4.13		FR 4 13
(Phases)	[MJ]	[MJ]	[MJ]	[MJ]	[MJ]	[MJ]