

Designation: awropi31a-02 Last updated: 8/2/23

Source: Holzforschung Austria

Editor: HFA, SP

# External wall - awropi31a-02


external wall, timber frame construction, not ventilated, with dry lining, with rendering, other surface

#### Performance rating

 $\begin{tabular}{lll} Fire protection & REI from inside & 60 \\ performance & REI from outside & 90 \\ maximum ceiling height = 3 m; maximum load <math>E_{d,fi} = 32,0 \ kN/m \\ Classified by HFA \\ \end{tabular}$ 

Thermal performance	U Diffusion	0.12 W/(m <sup>2</sup> K) suitable
Calculated by HFA		
Acoustic performance	R <sub>w</sub> (C;C <sub>tr</sub> ) L <sub>n,w</sub> (C <sub>l</sub> )	46(-2;-8) dB
frequency range 50-3500 Assessed by HFA	: C50-3500 -8 dB; Ct	r 50-3500 -19 dB

 $\text{Mass per unit area} \qquad \qquad \qquad \qquad \qquad \qquad 76.60 \; \text{kg/m}^2$ 

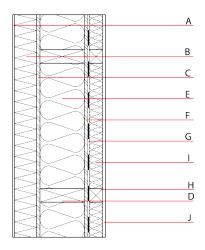

## Register of building materials used for this application, cross-section (from outside to inside, dimensions in mm)

	Thickness	Building material	Thermal performance			Reaction to fire	
			λ	μ min – max	ρ	С	EN
Α	7.0	plaster	1.000	10 - 35	2000	1.130	A1
В	100.0		0.040	1	100	1.030	A1
С	15.0	OSB	0.130	200	600	1.700	D
D	200.0	construction timber (60/; e=625)	0.120	50	450	1.600	D
E	200.0	Cellulose fibre [040; 50]	0.040	1	50	2.000	E
F	15.0	OSB	0.130	200	600	1.700	D
G		vapour barrier sd≥ 14m					
Н	60.0	spruce wood - cross battens (60/60) vertical (a=625)	0.120	50	450	1.600	D
ı	60.0	Cellulose fibre [040; 50]	0.040	1	50	2.000	E
J	12.5	gypsum plaster board type DF or	0.250	10	800	1.050	A2
J	12.5	gypsum fibre board	0.320	21	1000	1.100	A2

### Sustainability rating (per m<sup>2</sup>)

Database ecoinvent
OI3<sub>Kon</sub> 51.3

Calculated by HFA



Designation: awropi31a-02 Last updated:

8/2/23 Holzforschung Austria Source:

Editor: HFA, SP

## Details of sustainability rating

#### Database ecoinvent

Lifecycle	GWP	AP	EP	ODP	POCP	
(Phases)	[kg CO <sub>2</sub> -e.]	[kg SO <sub>2</sub> -e.]	[kg PO <sub>4</sub> -e.]	[kg R11-e.]	[kg Ethen-e.]	
A1 - A3		0.251	0.085	2,97E-6	0.074	
Lifecycle	PERE	PERM	PERT	PENRE	PENRM	PENRT
(Phases)	[MJ]	[MJ]	[MJ]	[MJ]	[MJ]	[MJ]
A1 - A3	126.000	653.626	779.626	611.663	28.482	640.145