

External wall - awropo22b-17

external wall, timber frame construction, not ventilated, without dry lining, with rendering, other surface

Performance rating

Fire protection performance REI from inside 60
 REI from outside 60
 maximum ceiling height = 3 m; maximum load $E_{d,fi} = 32 \text{ kN/m}$
 Classified by HFA
 Classified by HFA

Germany

F60 (from inside/from outside)
 Load $E_{d,fi}$ according to the German certification document
 Corresponding proof: manufacturer-specific

Thermal performance U Diffusion 0.14 $\text{W}/(\text{m}^2\text{K})$
 suitable


Calculated by TUM

Acoustic performance $R_w (C; C_{tr})$ 53(-2;-8) dB
 $L_{n,w} (C_i)$

Assessed by Müller-BBM

Mass per unit area m 80.10 kg/m^2

Calculation based on gypsum plaster board type DF

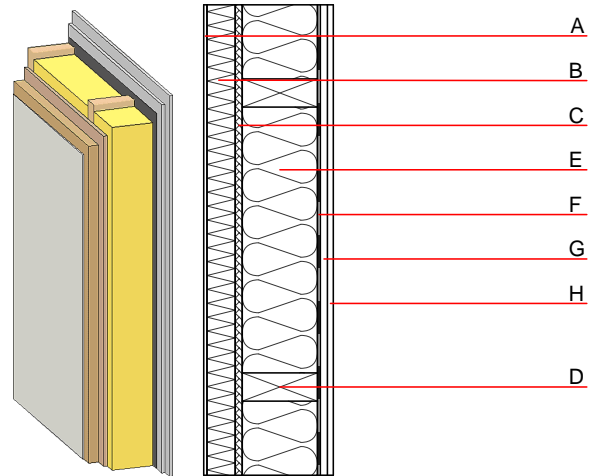

Register of building materials used for this application, cross-section (from outside to inside, dimensions in mm)

	Thickness	Building material	Thermal performance				Reaction to fire EN
			λ	μ min - max	ρ	c	
A	7.0	plaster	1.000	10 - 35	2000	1.130	A1
B	60.0	wood-fibre insulation board [055; 200]	0.055	5 - 7	200	2.100	E
C	15.0	fibreboard (MDF)	0.140	11	600	1.700	D
D	240.0	construction timber (60/..; e=625)	0.120	50	450	1.600	D
E	240.0	Wood fibre insulation [039; 45]	0.039	1 - 2	45	2.100	E
F		vapour barrier $s_d \geq 3\text{m}$			1000		
G	15.0	gypsum fibre board	0.320	21	1000	1.100	A2
H	12.5	gypsum fibre board or	0.320	21	1000	1.100	A2
H	12.5	gypsum plaster board type DF	0.250	10	800	1.050	A2

Sustainability rating (per m^2)

Database ecoinvent

$O13_{kon}$ 38.2

Calculated by HFA

Database GaBi (ÖKOBAUDAT)

Built-in renewable materials kg 48.150
Biogenic carbon in $\text{kg CO}_2\text{-e}$. kg CO_2 68.460
Energy use of Primary Energy MJ 1172.390
Share of renewable PE % 36.88

Calculated by TUM

Details of sustainability rating

Database ecoinvent

Lifecycle (Phases)	GWP [kg CO ₂ -e.]	AP [kg SO ₂ -e.]	EP [kg PO ₄ -e.]	ODP [kg R11-e.]	POCP [kg Ethen-e.]	
A1 - A3		0.163	0.069	3,29E-6	0.023	

Lifecycle (Phases)	PERE [MJ]	PERM [MJ]	PERT [MJ]	PENRE [MJ]	PENRM [MJ]	PENRT [MJ]
A1 - A3	147.600	690.847	838.447	603.286	56.580	659.867

Database GaBi (ÖKOBAUDAT)

Lifecycle (Phases)	GWP [kg CO ₂ -e.]	AP [kg SO ₂ -e.]	EP [kg PO ₄ -e.]	ODP [kg R11-e.]	POCP [kg Ethen-e.]	
A1 - A3		0.130	0.029	1,44E-6	0.028	
C1 - C4		0.004	0.001	9,51E-8	0.000	
A1 - C4		0.138	0.031	1,55E-6	0.029	

Lifecycle (Phases)	PERE [MJ]	PERM [MJ]	PERT [MJ]	PENRE [MJ]	PENRM [MJ]	PENRT [MJ]
A1 - A3	429.516	1077.330	1508.067	697.995	74.587	772.690
C1 - C4	1.998	-1067.766	-1065.603	30.199	-64.105	-31.700
A1 - C4	432.372	10.082	444.044	740.016	10.598	756.300