

Designation: fdrhbi10b-04 8/2/23 Last updated:

Holzforschung Austria Source:

Editor: HFA, SP

## Flat roof - fdrhbi10b-04

flat roof, timber frame construction, ventilated, with dry lining, not suspended, other surface


#### Performance rating


Fire protection

performance maximum span = 5 m; maximum load  $E_{d,fi}$  = 3,66 kN/m<sup>2</sup> Classified by HFA Thermal performance U  $0.16 \text{ W/(m}^2\text{K)}$ Diffusion suitable Calculated by HFA Acoustic performance  $R_w$  (C;C<sub>tr</sub>) 49(-3;-7) dB  $L_{n,w}$  ( $C_{l}$ ) Assessed by TGM

Mass per unit area  $64.80 \text{ kg/m}^2$ Calculation based on GF

60

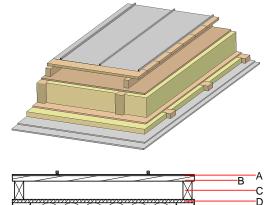



Note: The design of the under-roof construction and of the counterbattens have to be specified according to the roof pitch and the national requirements.

# Register of building materials used for this application, cross-section (from outside to inside, dimensions in mm)

	Thickness	Building material	Thermal per	rformance			Reaction to fire
			λ	μ min – max	ρ	С	EN
Α		Plastic roofing membrane or					Е
Α		sheet metal roofing			7800		A1
В	24.0	spruce wood closed cladding without spacing of cladding boards	0.120	50	450	1.600	D
С	80.0	spruce wood counter battens (ventilation)	0.120	50	450	1.600	D
D		sarking membrane sd ≤ 0,3 m			1000		Е
D	15.0	fibreboard (MDF)	0.140	11	600	1.700	D
Е	200.0	construction timber (80/; e=800)	0.120	50	450	1.600	D
F	200.0	mineral wool [035; 50; <1000°C]	0.035	1	50	1.030	A1
G	15.0	OSB (sealed with airtight tape)	0.130	200	600	1.700	D
Н	50.0	spruce wood cross battens (50/80;a=400)	0.120	50	450	1.600	D
1	50.0	mineral wool [035; 50; <1000°C]	0.035	1	50	1.030	A1
J	25.0	gypsum plaster board type DF (2x12,5 mm) or	0.250	10	800	1.050	A2
J	25.0	gypsum fibre board (2x12,5 mm)	0.320	21	1000	1.100	A2

## Sustainability rating (per m<sup>2</sup>)

Calculated by HFA

Database ecoinvent OI3<sub>Kon</sub> 69.2



Designation: fdrhbi10b-04 8/2/23 Holzforschung Austria Last updated:

Source:

HFA, SP Editor:

#### Details of sustainability rating

#### Database ecoinvent

Lifecycle	GWP	AP	EP	ODP	POCP	
(Phases)	[kg CO <sub>2</sub> -e.]	[kg SO <sub>2</sub> -e.]	[kg PO <sub>4</sub> -e.]	[kg R11-e.]	[kg Ethen-e.]	
A1 - A3		0.297	0.137	4,95E-6	0.047	
Lifecycle	PERE	PERM	PERT	PENRE	PENRM	PENRT
Lifecycle (Phases)	PERE [MJ]	PERM [MJ]	PERT [MJ]	PENRE [MJ]	PENRM [MJ]	PENRT [MJ]