

Designation: fdrhbi10b-05 8/2/23 Last updated:

Holzforschung Austria Source:

Editor: HFA, SP

## Flat roof - fdrhbi10b-05

flat roof, timber frame construction, ventilated, with dry lining, not suspended, other surface

### Performance rating

Fire protection


Mass per unit area

Calculated by HFA

Calculation based on GF

performance maximum span = 5 m; maximum load  $E_{d,fi}$  = 3,66 kN/m<sup>2</sup> Classified by HFA Thermal performance U  $0.18 \text{ W/(m}^2\text{K)}$ Diffusion suitable Calculated by HFA Acoustic performance  $R_w$  (C;C<sub>tr</sub>) 48(-2;-6) dB  $L_{n,w}$  ( $C_{l}$ ) Assessed by TGM

60

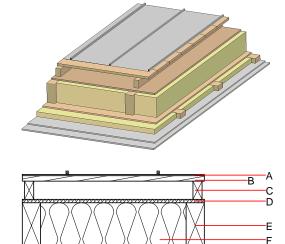

Note: The design of the under-roof construction and of the counterbattens have to be specified according to the roof pitch and the national requirements.

H/I

### Register of building materials used for this application, cross-section (from outside to inside, dimensions in mm)

 $61.00 \text{ kg/m}^2$ 

	Thickness	Building material	Thermal performance				Reaction to fire	
			λ	μ min – max	ρ	С	EN	
Α		Plastic roofing membrane or					E	
Α		sheet metal roofing			7800		A1	
В	24.0	spruce wood closed cladding without spacing of cladding boards	0.120	50	450	1.600	D	
С	80.0	spruce wood counter battens (ventilation)	0.120	50	450	1.600	D	
D		sarking membrane sd ≤ 0,3 m			1000		Е	
D	15.0	fibreboard (MDF)	0.140	11	600	1.700	D	
E	200.0	construction timber (80/; e=800)	0.120	50	450	1.600	D	
F	200.0	mineral wool [038; ≥33; ≥1000°C]	0.038	1	33	1.030	A1	
G	15.0	OSB (sealed with airtight tape)	0.130	200	600	1.700	D	
Н	50.0	spruce wood cross battens (50/80;a=400)	0.120	50	450	1.600	D	
1	50.0	mineral wool [038; ≥33; ≥1000°C]	0.038	1	33	1.030	A1	
J	25.0	gypsum plaster board type DF (2x12,5 mm) or	0.250	10	800	1.050	A2	
J	25.0	gypsum fibre board (2x12,5 mm)	0.320	21	1000	1.100	A2	

# Sustainability rating (per m<sup>2</sup>) Database ecoinvent OI3<sub>Kon</sub> 48.7



Designation: fdrhbi10b-05 Last updated:

8/2/23 Holzforschung Austria Source:

Editor: HFA, SP

### Details of sustainability rating

#### Database ecoinvent

Lifecycle	GWP	AP	EP	ODP	POCP	
(Phases)	[kg CO <sub>2</sub> -e.]	[kg SO <sub>2</sub> -e.]	[kg PO <sub>4</sub> -e.]	[kg R11-e.]	[kg Ethen-e.]	
A1 - A3		0.237	0.089	2,70E-6	0.073	
Lifecycle	PERE	PERM	PERT	PENRE	PENRM	PENRT
		1				
(Phases)	[MJ]	[MJ]	[MJ]	[MJ]	[MJ]	[MJ]