

Designation: gdrnxa07a-14 8/2/23 Last updated:

Holzforschung Austria Source:

Editor: HFA, SP

Intermediate floor - gdrnxa07a-14

intermediate floor, timber frame construction, suspended, wet, with filling, other surface

Performance rating

Fire protection REI performance

maximum span = 5 m; maximum load $E_{d,fi}$ = 3,66 kN/m² (without floor construction; with ceiling beam 80/200)

Classified by HFA

Classified by HFA

Germany


F30


Load $E_{d,fi}$ according to the German certification document

Corresponding proof: DIN 4102-4:2016-05, Tabelle 10.12, Zeile 1

Thermal performance	U Diffusion	suitable
Calculated by HFA		
Acoustic performance	R _w (C;C _{tr}) L _{n,w} (C _l)	69(-1;-6) dB 42(2)
Assessed by Müller-BBM		
Mass per unit area	m	199.30 kg/m ²

Calculation based on gypsum plaster board type DF

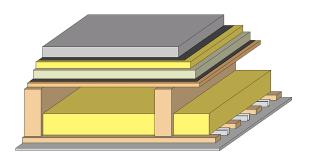

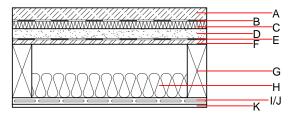

Register of building materials used for this application, cross-section (from outside to inside, dimensions in mm)

	Thickness	Building material	Thermal performance				Reaction to fire
			λ	μ min – max	ρ	С	EN
A	50.0	cement screed or anhydrite screed	1.330	50 - 100	2000	1.080	A1
3		plastic separation layer		100000	1400	1.400	E
2	40.0	impact sound absorbing subflooring MW-T [s' = 10 MN/m³]	0.035	1	68	1.030	A1
)	30.0	fill loose	0.700	1	1800	1.000	A1
		trickling protection					E
=	18.0	OSB	0.130	200	600	1.700	D
5	240.0	construction timber (80/; e=625)	0.120	50	450	1.600	D
1	100.0	Cellulose fibre [040; 50]	0.040	1	50	2.000	E
	24.0	spruce wood cladding with spacing of cladding boards(24/100); a=400	0.120	50	450	1.600	D
	27.0	resilient channel placed between cladding with spacing	0.156				
	12.5	gypsum plaster board type DF or	0.250	10	800	1.050	A2
(12.5	gypsum fibre board	0.320	21	1000	1.100	A2

Sustainability rating (per m²)

Database ecoinvent		Database GaBi (ÖKOBAUDAT)				
Ol3 _{Kon} Calculated by HFA	38.5	Built-in renewable materials Biogenic carbon in kg CO ₂ -e. Energy use of Primary Energy Share of renewable PE	kg kg CO ₂ MJ %	34.520 50.160 655.310 22.88		



Designation: gdrnxa07a-14 Last updated:

8/2/23 Holzforschung Austria Source:

Editor: HFA, SP

Details of sustainability rating

Database ecoinvent

Lifecycle	GWP	AP	EP	ODP	POCP	
(Phases)	[kg CO ₂ -e.]	[kg SO ₂ -e.]	[kg PO ₄ -e.]	[kg R11-e.]	[kg Ethen-e.]	
A1 - A3		0.161	0.077	2,67E-6	0.029	
Lifecycle	PERE	PERM	PERT	PENRE	PENRM	PENRT
(Phases)	[MJ]	[MJ]	[MJ]	[MJ]	[MJ]	[MJ]
A1 - A3	114.580	519.976	634.556	544.007	20.654	564.661

Database GaBi (ÖKOBAUDAT)

Lifecycle	GWP	AP	EP	ODP	POCP
(Phases)	[kg CO ₂ -e.]	[kg SO ₂ -e.]	[kg PO ₄ -e.]	[kg R11-e.]	[kg Ethen-e.]
A1 - A3		0.129	0.019	8,16E-7	0.022
C1 - C4		0.016	0.007	7,73E-8	0.002
A1 - C4		0.150	0.027	9,01E-7	0.023

Lifecycle	PERE	PERM	PERT	PENRE	PENRM	PENRT
(Phases)	[MJ]	[MJ]	[MJ]	[MJ]	[MJ]	[MJ]
A1 - A3	147.317	576.747	725.612	475.955	50.466	526.570
C1 - C4	2.215	-498.594	-495.240	23.981	-7.744	31.837
A1 - C4	149.913	78.412	231.496	505.396	42.774	572.058