

Designation: gdrnxa07a-05 Last updated: 8/2/23

Source: Holzforschung Austria

Editor: HFA, SP

Intermediate floor - gdrnxa07a-05

intermediate floor, timber frame construction, suspended, wet, with filling, other surface

Performance rating

Fire protection REI 30 performance

maximum span = 5 m; maximum load $E_{d,\rm fi}$ = 3,66 kN/m² (without floor construction; with ceiling beam 80/200)

Classified by IBS

Classified by HFA

Mass per unit area

Germany


F30


Load $E_{\text{d,fi}}$ according to the German certification document

Corresponding proof: DIN 4102-4:2016-05, Tabelle 10.12, Zeile 1

Thermal performance	U Diffusion	0.26 W/(m ² K) suitable
Calculated by HFA		
Acoustic performance	R _w (C;C _{tr})	70(-1;-6) dB
	$L_{n,w}$ (C_{l})	41(1)
ssessed by TGM		
Assessed by Müller-BBM		

Calculation based on gypsum plaster board type DF

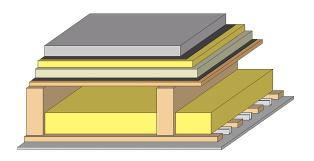

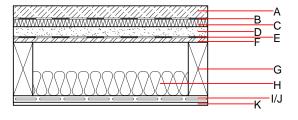

Register of building materials used for this application, cross-section (from outside to inside, dimensions in mm)

215.90 kg/m²

	Thickness	Building material	Thermal performance				Reaction to fire
			λ	μ min – max	ρ	С	EN
4	50.0	cement screed or anhydrite screed		50 - 100	2000	1.080	A1
3		plastic separation layer	0.200	100000	1400	1.400	E
2	30.0	impact sound absorbing subflooring MW-T [s' = 10 MN/m³]		1	68	1.030	A1
)	40.0	fill loose	0.700	1	1800	1.000	A1
		trickling protection					E
	18.0	OSB	0.130	200	600	1.700	D
5	220.0	construction timber (80/; e=625)	0.120	50	450	1.600	D
1	100.0	cellulose fibre [040; E]	0.040	1 - 2	55	2.000	E
	24.0	spruce wood cladding with spacing of cladding boards(24/100); a=400	0.120	50	450	1.600	D
	27.0	resilient channel placed between cladding with spacing	0.156				
	12.5	gypsum plaster board type DF or	0.250	10	800	1.050	A2
<	12.5	gypsum fibre board	0.320	21	1000	1.100	A2

Sustainability rating (per m²)

Databasa sasimusut

Database econvent		Database Gabi (OKOBAODAT)				
OI3 _{Kon}	35.5	Built-in renewable materials	kg	33.260		
Calculated by HFA		Biogenic carbon in kg CO ₂ -e.	kg CO₂	48.320		
Carcalated by Till A		Energy use of Primary Energy	MJ	646.270		
		Share of renewable PE	%	22.46		

Database Call: (ÖKORALIDAT)



gdrnxa07a-05 Designation: Last updated:

8/2/23 Holzforschung Austria Source:

Editor: HFA, SP

Details of sustainability rating

Database ecoinvent

Lifecycle	GWP	AP	EP	ODP	POCP	
(Phases)	[kg CO ₂ -e.]	[kg SO ₂ -e.]	[kg PO ₄ -e.]	[kg R11-e.]	[kg Ethen-e.]	
A1 - A3		0.148	0.071	2.45E-6	0.027	
Lifecycle	PERE	PERM	PERT	PENRE	PENRM	PENRT
(Phases)	[MJ]	[MJ]	[MJ]	[MJ]	[MJ]	[MJ]
A1 - A3	109.193	499.012	608.205	504.925	20.654	525.579

Database GaBi (ÖKOBAUDAT)

Lifecycle	GWP	AP	EP	ODP	POCP
(Phases)	[kg CO ₂ -e.]	[kg SO ₂ -e.]	[kg PO ₄ -e.]	[kg R11-e.]	[kg Ethen-e.]
A1 - A3		0.128	0.019	7.79E-7	0.022
C1 - C4		0.016	0.007	7.43E-8	0.002
A1 - C4		0.148	0.027	8.61E-7	0.023

Lifecycle	PERE	PERM	PERT	PENRE	PENRM	PENRT
(Phases)	[MJ]	[MJ]	[MJ]	[MJ]	[MJ]	[MJ]
A1 - A3	142.581	554.961	698.988	471.910	50.453	522.499
C1 - C4	2.203	-476.814	-473.472	23.740	-7.731	31.610
A1 - C4	145.165	78.406	226.640	501.110	42.774	567.760