

Designation: gdrnxa08a-09 8/2/23 Last updated:

Holzforschung Austria Source:

Editor: HFA, SP

Intermediate floor - gdrnxa08a-09

intermediate floor, timber frame construction, suspended, wet, with filling, other surface

Performance rating

Classified by HFA

30 Fire protection performance maximum span = 5 m; maximum load $E_{d,fi}$ = 3,66 kN/m²

Thermal performance U $0.27 \text{ W/(m}^2\text{K)}$ Diffusion suitable


energy storage capacity per unit area above: 104,4 kg/m² Calculated by HFA


 R_w (C;C_{tr}) 65(-3;-8) dB Acoustic performance $L_{n,w}$ (C_l) 50(2)

EPS-F with a dynamic stiffness of $s' \le 40MN/m^3$.

Mass per unit area 214.40 kg/m²

Calculation based on gypsum plaster board type DF

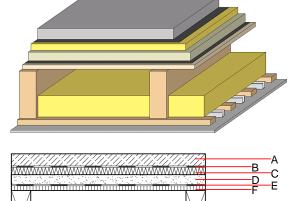



Note: e=625;

Register of building materials used for this application, cross-section (from outside to inside, dimensions in mm)

	Thickness	Building material	Thermal performance				Reaction to fire	
			λ	μ min – max	ρ	С	EN	
Α	50.0	cement screed or anhydrite screed	1.330	50 - 100	2000	1.080	A1	
В		plastic separation layer	0.200	100000	1400	1.400	E	
С	30.0	Polystyrene EPS-W [s¹≥26 MN/m³]	0.041	20 - 50	15	1.450	Е	
D	40.0	fill	0.700	1	1800	1.000	A1	
E		trickling protection					E	
F	19.0	particleboard	0.130	50 - 100	700	1.700	D	
G	220.0	construction timber (80/; e=*)	0.120	50	450	1.600	D	
Н	100.0	mineral wool [040; ≥16; <1000°C]	0.040	1	16	1.030	A1	
I	24.0	spruce wood cladding with spacing of cladding boards(24/100); a=400	0.120	50	450	1.600	D	
J	27.0	resilient channel placed between cladding with spacing	0.156					
K	12.5	gypsum plaster board type DF or	0.250	10	800	1.050	A2	
K	12.5	gypsum fibre board	0.320	21	1000	1.100	A2	

Sustainability rating (per m²)

Database ecoinvent OI3_{Kon} 34.1 Calculated by HFA



Designation: gdrnxa08a-09 8/2/23 Holzforschung Austria Last updated:

Source:

HFA, SP Editor:

Details of sustainability rating

Database ecoinvent

Lifecycle	GWP	AP	EP	ODP	POCP	
(Phases)	[kg CO ₂ -e.]	[kg SO ₂ -e.]	[kg PO ₄ -e.]	[kg R11-e.]	[kg Ethen-e.]	
A1 - A3		0.129	0.062	2,05E-6	0.030	
Lifecycle	PERE	PERM	PERT	PENRE	PENRM	PENRT
(Phases)	[MJ]	[MJ]	[MJ]	[MJ]	[MJ]	[MJ]
A1 - A3	74.813	473.735	548.548	505.014	53.059	558.074