

Designation: gdrtxn03b-03 8/2/23 Last updated:

Holzforschung Austria Source:

Editor: HFA, SP

Intermediate floor - gdrtxn03b-03

intermediate floor, timber frame construction, not suspended, dry, without filling, other surface


Performance rating

Fire protection

performance maximum span = 5 m; maximum load $E_{d,fi}$ = 3,66 kN/m² Classified by HFA Thermal performance U $0.25 \text{ W/(m}^2\text{K)}$ Diffusion suitable Calculated by HFA Acoustic performance R_w (C;C_{tr}) 50(-2;-9) dB $L_{n,w}$ (C_{l}) 66(0) Assessed by TGM Mass per unit area

60

Calculation based on GF

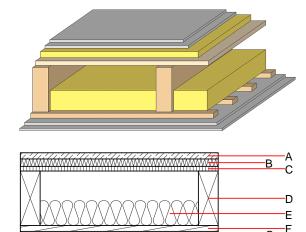

Note: e=625;

Register of building materials used for this application, cross-section (from outside to inside, dimensions in mm)

 76.90 kg/m^2

| | Thickness | Building material | Thermal per | rformance | | | Reaction to fire |
|---|-----------|------------------------------------------------------------------------|-------------|-------------|------|-------|------------------|
| | | | λ | μ min – max | ρ | С | EN |
| Α | 25.0 | dry screed | 0.210 | 8 | 900 | 1.050 | A1 |
| В | 30.0 | impact sound absorbing subflooring MW-T | 0.035 | 1 | 68 | 1.030 | A1 |
| С | 19.0 | particleboard | 0.130 | 50 - 100 | 700 | 1.700 | D |
| D | 220.0 | construction timber (80/; e=*) | 0.120 | 50 | 450 | 1.600 | D |
| Е | 100.0 | mineral wool [035; 50; <1000°C] | 0.035 | 1 | 50 | 1.030 | A1 |
| F | 24.0 | spruce wood cladding with spacing of cladding boards(24/100); a=400 $$ | 0.120 | 50 | 450 | 1.600 | D |
| G | 25.0 | gypsum plaster board type DF (2x12,5 mm) or | 0.250 | 10 | 800 | 1.050 | A2 |
| G | 25.0 | gypsum fibre board (2x12,5 mm) | 0.320 | 21 | 1000 | 1.100 | A2 |

Sustainability rating (per m²)

Database ecoinvent

 013_{Kon} 42.1

Calculated by HFA



Designation: gdrtxn03b-03 8/2/23 Holzforschung Austria Last updated:

Source:

Editor: HFA, SP

Details of sustainability rating

Database ecoinvent

| Lifecycle | GWP | AP | EP | ODP | POCP | |
|-----------|--------------------------|--------------------------|--------------------------|-------------|---------------|---------|
| (Phases) | [kg CO ₂ -e.] | [kg SO ₂ -e.] | [kg PO ₄ -e.] | [kg R11-e.] | [kg Ethen-e.] | |
| A1 - A3 | | 0.164 | 0.074 | 3,43E-6 | 0.029 | |
| | | | | | | |
| Lifecycle | PERE | PERM | PERT | PENRE | PENRM | PENRT |
| (Phases) | [MJ] | [MJ] | [MJ] | [MJ] | [MJ] | [MJ] |
| A1 - A3 | 77.224 | 473.735 | 550.959 | 638.874 | 29.215 | 668.089 |