

Designation: sdrhzi04b-05 Last updated: 8/2/23

Holzforschung Austria Source:

Editor: HFA, SP

Pitched roof - sdrhzi04b-05

pitched roof, timber frame construction, ventilated, with dry lining, not suspended, other surface

Performance rating

Fire protection

performance maximum span = 5 m; maximum load $E_{d,fi}$ = 3,66 kN/m² Classified by HFA Thermal performance U $0.19 \text{ W/(m}^2\text{K)}$ Diffusion suitable Calculated by HFA


60

Acoustic performance R_w (C;C_{tr}) 55(-2;-8) dB $L_{n,w}$ (C_I)

with a tiled roof Rw = 53 (-2; -8) dBAssessed by TGM

Mass per unit area 58.20 kg/m^2

Calculation based on gypsum plaster board type DF

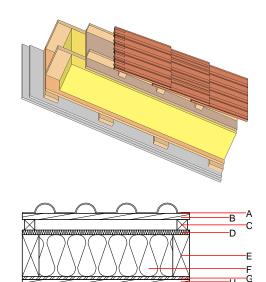

Note: The design of the under-roof construction and of the counterbattens have to be specified according to the roof pitch and the national requirements.

Register of building materials used for this application, cross-section (from outside to inside, dimensions in mm)

	Thickness	Building material	Thermal per	rformance			Reaction to fire
			λ	μ min – max	ρ	С	EN
Α		concrete roof tile or tiled roof			2100		A1
В	30.0	spruce wood battens (30/50)	0.120	50	450	1.600	D
С	50.0	spruce wood counter battens (minimum height 50 mm)	0.120	50	450	1.600	D
D	22.0	softboard [045; 250] - rigid underlay	0.045	5	250	2.100	E
E	200.0	construction timber (80/; e=800)	0.120	50	450	1.600	D
F	200.0	cellulose fibre [040; E]	0.040	1 - 2	55	2.000	E
G	15.0	OSB (sealed with airtight tape)	0.130	200	600	1.700	D
Н	24.0	spruce wood cladding with spacing of cladding boards(24/100); a=400	0.120	50	450	1.600	D
I	25.0	gypsum plaster board type DF (2x12,5 mm) or	0.250	10	800	1.050	A2
I	25.0	gypsum fibre board (2x12,5 mm)	0.320	21	1000	1.100	A2

Sustainability rating (per m²)

Database ecoinvent									
Ol3 _{Kon}	24.5								
Calculated by HFA									



Designation: sdrhzi04b-05 Last updated:

8/2/23 Holzforschung Austria Source:

HFA, SP Editor:

Details of sustainability rating

Database ecoinvent

Lifecycle	GWP	AP	EP	ODP	POCP	
(Phases)	[kg CO ₂ -e.]	[kg SO ₂ -e.]	[kg PO ₄ -e.]	[kg R11-e.]	[kg Ethen-e.]	
A1 - A3		0.113	0.050	2,74E-6	0.021	
Lifecycle	PERE	PERM	PERT	PENRE	PENRM	PENRT
(Phases)	[MJ]	[MJ]	[MJ]	[MJ]	[MJ]	[MJ]
A1 - A3	101.945	623.844	725.790	415.520	19.362	434.882